

PRESERVATION OF DURIAN TIMBER AND COCONUT TIMBER WITH SOURSOP LEAF EXTRACT

by Sri Handayani

Submission date: 25-Sep-2018 12:14PM (UTC+0700)

Submission ID: 1007950116

File name: Handayani_SCESCM.pdf (576.42K)

Word count: 2858

Character count: 14902

PRESERVATION OF DURIAN TIMBER AND COCONUT TIMBER WITH SOURSOP LEAF EXTRACT

Sri Handayani¹, Endah Kanti Pangestuti² and Ninda Adhitya Dharma³

4

¹Department of Civil Engineering, Universitas Negeri Semarang (UNNES), 50229, Semarang, Indonesia

²Department of Civil Engineering, Universitas Negeri Semarang (UNNES), 50229, Semarang, Indonesia

³Department of Civil Engineering, Universitas Negeri Semarang (UNNES), 50229, Semarang, Indonesia

Abstract : Durian timber and Coconut timber grow a lot in the area of Gunung Pati Semarang, Central Java. The threat of biodegradation in Indonesia as tropical area is quite high. Therefore, it is necessary to take protection measures in the form of preservation for prevention. The preservatives used in this study are natural preservative of soursop leaf extract. The preservation method used was cold soaking method with variation of concentration of preservative as follows: 0%, 5%, 10%, 15%, 20% and 25%. This study aims to figure out how significant the weight loss of timber and how durian wood and coconut wood's resistance to termites based on the weight loss of timber. Result of examination of termite attack on Coconut timber with preservation of soursop leaf extract 0%, 5%, 10%, 15%, 20% and 25% obtained by weight loss of wood 17.57%, 13.43%, 10.61%, 7.67%, 5.50% and 4.20%. Meanwhile, the result of examination of termite attack on Durian timber with the concentration of soursop leaf extract 0%, 5%, 10%, 15%, 20% and 25% showed these following timber weight losses: 18.24%, 14.61%, 13.04%, 11.33%, 8.98% and 7.84%. Based on the wood resistance table, Durian timber with soursop leaf concentration of 20% and 25% were classified in the medium classification. Coconut timber with 15% and 20% soursop leaf concentrations were classified in the medium classification, while at 25% concentrations in resistant classification.

Keywords: preservation, soursop leaf extract, termite test

1. Introduction

Good quality timber demand is increasing as the population grows. However, nowadays, it is very difficult to obtain raw materials of a very high quality wood from natural forests. This causes the focus of timber utilization from natural forests to switch to community forests and plantations. Durian and coconut timbers are the commodities which are now starting to be utilized. Durian and coconut timbers grow and are found in tropical climates. The timber originating from community forests and plantations differs in nature from timber derived from natural forests [1]. The timbers from contemporary people's forest has not seen its properties especially its durability and durability. Timber from the forest is basically used for various purposes both for carpentry and building materials. However, its use should be supported by technologies that can improve the properties of wood, such as sawmill, drying, pickling, and other processing technology [2].

The durability of wood is also influenced by several factors such as extractive substance content in wood, age of time tree fell, place of tree, tree origin (natural forest or plantation), tree varieties, tree growth rate, where wood is used and treat silviculture [3].

The threat of biodegradation in Indonesia as tropical area is quite high, therefore, it is necessary to take protection measures in the form of preservation for prevention. Timber from community forest is expected to be a substitute material of wood from natural forests both for the needs of building components and industrial raw

materials. Coconut timber is also known as glugu timber is a timber obtained from the collection of good coconut trees that grow wildly and cultivated as one part of the coconut tree [4]. The average density of Coconut timber is 0.74 then it belongs to the strong class II (specific gravity 0.6 - 0.9). Coconut timber is included in the durable class III.

Durian timber properties are classified as class II-III with specific gravity of 0.57. Durian timber belongs to the class of durability IV-V and strong class II-III. Wood is classified as relatively light wood species and has a relatively low durability [5]. Timber preservation with the addition of montan and boric acid wax emulsions for 20% up to 50% in timber, providing protection from timber rotting fungi [6].

The research had managed to overcome the problem by determine the amount suitable for the rubber timber. Converting acetic and butyric acids derived from landfill leachate into acetate and butyrate salt, leachate can be fermented and be potentially turned into a valuable timber preservative. The mixture of sodium acetate and sodium butyrate can be a preservative in rubber timber because it can inhibit the growth of timber rotting fungi [7].

Borates prevents fungal decay and are deadly to termites, carpenter ants and roaches - but safe for people and the environment. Boron is not fixed chemically to timber, and it will be leached out if timber in service is subjected to an wet environment [8].

The use of bamboo for building materials, especially in the use as a construction, needs a maximum bamboo handling with preservative borax [9]

Termites especially *Coptotermes* sp. has a wide distribution and has caused severe damage. Various chemicals have been used to cope with the danger of termite attack. However, the use of such chemicals can endanger the environment [10].

Therefore, the chemical materials must be replaced with the use of natural materials for preservatives. From the potential of environmentally friendly soursop leaf extract as an insecticide, it can be used *Coptotermes* sp as termite controller. Soursop leaves can act as insecticide, larvacide, repellent (insect repellent) and inhibitor. Soursop leaf contains acetogenin compound, such as asimisin, bulatacin and squamosin [11]

The results of the study presented by Grainge and Ahmed (1989) reported that the active ingredients contained by soursop seeds such as alkaloids, annonain, mauricine, and mauricinine may act as antifeedants and insecticides [12]

Soursop leaf extract contains 66% of monoterpene compounds and 28% sesquiterpene. In addition, it also contains 11-17% α -pinene, 12.5-24.8% cymene, and 10.6% thymyl acetate [13].

Soursop leaf powder can stop the growth of termites and increase termite mortality [14]

The result of this research shows that the flour of soursop leaf from dosage 0,5 gr/100gr grain has an effect on the increasing mortality and decreasing the growth of beetle soybean powder (*C. analis*) on soy grain and can decrease the decay and soy grain weight caused by the attack of beetle soybean powder (*C. analis*) at any deviation. Key words : The flour of sorsop leaf (*Annona muricata*); the beetle of soy powder (*Callosobruchus analis* F.) [15].

2. Materials and Methods

2.1. Materials preparation

The research was conducted at UNNES Civil Engineering Laboratory. This research was an experimental research examining termite attack on Durian timber and Coconut timber. The treatment of this study was the preservation by using natural preservative of soursop leaf extract. The timbers used in this research were Durian timber and Coconut timber obtained in Gunungpati District Semarang.

The 30 pieces on Durian Timber and 30 pieces on Coconut Timber with 25mm width, height 25mm and tick 5mm were used as the test specimens .

Preparation of the test was carried out according to SNI 03-6847-2002 [16] about the Method of Testing the Heavy Type of Wood and Material Of Wood With The Immersion In Water and SNI 03-6850-2002 [17] on Test Method of Measurement of Wood Water Content and Wood Material

Termite resistance evaluation of the timbers was carried out referring to SNI 01-7207-2006 [18], which included the material preparation, test procedures and statements.

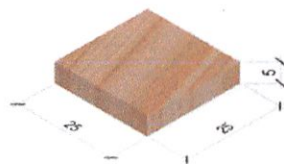


Figure 1. Size of the specimen

Method of preservation of timber was performed using cold soaking method. The preservatives used in this study were soursop leaf extract with these following variations of concentration: 0%, 5%, 10%, 15%, 20%, and 25%. Extraction process was obtained by soaking the soursop leaves that have been cleaned into water inside of containers and was allowed to cool down for 2-3 hours. After the water cooled down, the soursop leaf extract was ready for use as a natural timber preservative.

2.2. Data Analysis

The amount of specimen weight loss was calculated using this following equation :

$$P = \frac{W1 - W2}{W2} \times 100\% \quad (1)$$

Keterangan :

P : weight Loss (%)

W1 : Weight of specimen before termited test (g)

W2 : Weight of specimen after termited test (g)

Furthermore, the determination of termite resistance of the timber was based on the classification of timber resistance to termites based on weight loss, as shown in table 1.

Tabel 1. Classification of Timber Resistance to Termites Based on Weight Loss

Class	Resistance	Weight Loss (%)
I	Very resistant	$\leq 3,52$
II	resistant	3,25-7,50
III	Medium resistant	7,30-10,96
IV	Bad resistant	10,96-18,94
V	Very bad resistant	18,94-31,89

3. Results and Discussion

3.1. Water Content

Table 2. Water Content of Durian and Coconut Timber

No of Test Speciment	Water content (%)	
	Durian Timber	Coconut Timber
1	17.21	18.86
2	18.85	15.90
3	16.65	15.89
4	17.29	16.33
5	16.59	16.77
Average	17.32	16.62

The water content test results of Durian are presented in Table 1. The average water content of Durian timber is 17.32 %. The average water content of Coconut Timber is 16.62 %. Water content of Durian Timber was more than that of Coconut Timber

3.2. Specific Gravity of the Timber

The specific gravity is the ratio of timber density to the water density at the same volume. The results of the specific gravity of Durian Timber can be seen in Table 3. The results of this test showed that the average specific gravity of Durian Timber was 0.43. Meanwhile, the average specific gravity of Coconut Timber was 0.53. Specific gravity of Durian Timber was less than specific gravity of Coconut Timber.

Table 3. The Specific Gravity of Durian and Coconut Timber

No Test Specimen	Specific gravity	
	Durian timber	Coconut timber
1	0.42	0.52
2	0.46	0.51
3	0.41	0.52
4	0.41	0.56
5	0.43	0.56
Average	0.43	0.53

The results showed an inverse relationship between timber water content and its specific gravity; higher water content of timber lead to the lower specific gravity, or vice versa.

3.3. The Analysis of Termite Attact Test of DurianTimber

Tabel 4. Weight Loss of Durian Timber and Coconut Timber

Code	Concentration of Preservative	Weight Loss (%)	
		Durian Timber	Coconut Timber
1	0%	18,24	17,57

2	5%	14,61	13,43
3	10%	13,04	10,61
4	15%	11,33	7,67
5	20%	8,98	5,50
6	25%	7,84	4,20

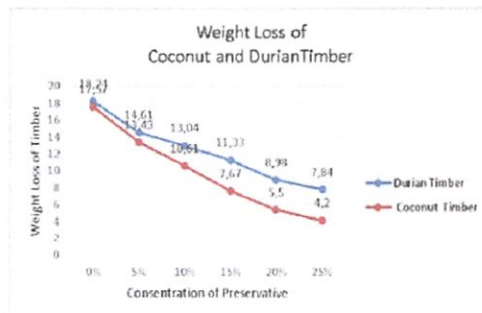


Figure 2. Weight loss of Durian and Coconut timber

Table 4. shows the average weight loss of timber of Durian timber and Coconut timber based on variation of soursop leaf extract concentration. Test results on Durian timber and Coconut timber showed the tendency of an inverse relationship. The higher content of soursop leaf extract led to the smaller weight loss of timber. This was caused by the higher content of soursop leaf extract into the timber, the cavities in the timber cells became more dense because it was filled by the amount of preservative (retention) from soursop leaf extracts. Therefore, the timber cells became more dense.

The results of the termite test also showed that the weight loss of Durian timber was higher compared with the weight loss of Coconut timber. This is in accordance with the test results of water content and specific gravity of Durian timber and Coconut timber. The specific gravity of Coconut timber (0.53) was higher than that of Durian timber (0.43). The higher specific gravity led to the lower timber weight loss. On the other hand, the lower specific gravity of timber led to the higher loss weight of timber.



Figure 3. Speciment test of Durian timber

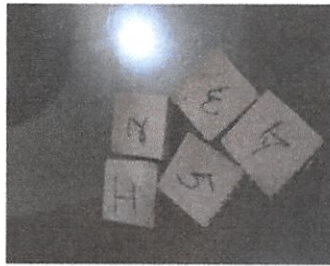


Figure 4. Specimen test of Coconut timber



Figure 5. Termites attack test



Figure 6. The specimens after termite

The result of analysis on timber resistance to termites based on weight loss, showed that the termite attack on Coconut timber with soursop leaf extract at 0%, 5%, 10%, 15%, 20% and 25% concentrations were presented in table 5.

Table 5. Durian Timber resistance to Termite attack

Code	Concentration of Preservative	Durian Timber	Class	Resistance
1	0%	18.24	IV	Bad
2	5%	14.61	IV	Bad
3	10%	13.04	IV	Bad
4	15%	11.33	IV	Bad
5	20%	8.98	III	Medium
6	25%	7.84	III	Medium

Table 6. Durian Timber resistance to Termite attack

Code	Concentration of Preservative	Coconut Timber	Class	Resistance
1	0%	17.57	IV	Bad
2	5%	13.43	IV	Bad
3	10%	10.61	IV	Bad
4	15%	7.67	III	Medium
5	20%	5.50	III	Medium
6	25%	4.20	III	Resistance

Table 5 shows that Durian timber resistance at 0% - 15% concentration is classified as bad, while 20% - 25% is classified as medium. Table 6 shows that Coconut timber resistance at 0% - 10% concentration is classified as bad, 15% - 20% is classified as medium, while at 25% concentration is classified as resistant.

Based on the results in tables 5 and 6, it shows that there is a difference in resistance in Coconut timber and Durian timber for the same concentration. Durian timbers with concentrations of 20% and 25% classified as medium. Meanwhile, Coconut Timber with concentration of 15% and 20% was classified as medium and 25% concentration was classified as resistant. This shows that the termite resistance of Coconut timber is higher than Durian timber.

4. Conclusions

Based on the results of research and data analysis on preservation of Durian timber and Coconut timber with soursop leaf extract that terminates tested can be concluded as follows

1. Weight loss of Durian timber is higher compared with weight loss of Coconut timber
2. The termite resistance on Coconut timber with soursop leaf extract 0%, 5%, 10%, 15%, 20% and 25% showed weight loss of 17.57%, 13.43%, 10.61%, 7.67%, 5.50% and 4.20%. Meanwhile, the result of examination of termite attack on Durian timber with the concentration of soursop leaf extract 0%, 5%, 10%, 15%, 20% and 25% showed the result of timber weight loss of 18.24%, 14.61%, 13.04%, 11.33%, 8.98% and 7.84%
3. The resistance of Coconut timber is higher than Durian timber. Durian timber with soursop leaf concentration of 20% and 25% was classified as medium. Coconut timber with 15% soursop leaf concentration and 20% was classified as medium. Meanwhile, the coconut timber at 25% concentration was classified as resistant.

5. References

- (1) Brazier. 1986. Perbedaan sifat kayu hutan alam dan hutan rakyat. Pusat Penelitian dan Pengembangan Hasil Hutan. Bogor
- (2) Abdurachman, Hadjib N. 2006. Pemanfaatan Kayu Hutan Rakyat untuk Komponen Bangunan. www.dephut.go.id/filesKomp_Bangunan.pdf. [3 Agustus 2009].
- (3) Martawijaya, A. (1996). Keawetan kayu dan factor yang mempengaruhinya. Petunjuk Teknis. Pusat penelitian dan Pengembangan Hasil Hutan dan Sosial Ekonomi Kehutanan. Bogor.
- (4) Indrosaptono, Djoko. Kayu Kelapa (Glugu) Sebagai Alternatif Bahan Konstruksi Bangunan, dalam Jurnal Arsitektur. Fakultas Teknik. Universitas Diponegoro Semarang. Volume 14 No. 1 Januari 2014
- (5) Oey Djoen Seng. 1990. Berat Jenis Dari Jenis – Jenis Kayu Indonesia dan Pengertian Beratnya Kayu untuk Keperluan Praktek. Nomor 1 Cetakan II. Soewarsono P.H., penerjemah: Bogor : Lembaga Penelitian Hasil Hutan. Terjemahan dari : Specific Gravity of Indonesian Woods and its Significance for Practical Use
- (6) Lesar, B et al (2009). Montan wax improves performance of boron-based wood preservatives. ELSEVIER. Volume 63.Issue 3, Pages 306-310
- (7) Syazwan, Muhammad; Abdulaziz, Hamidi; Azan, Huznul; Kwang, Kok. 2017. Preservation Of Rubber Timber Againsts Biological Decay By Salt Derived From Leachate. Timber Research 62(6): 2017 863-872
- (8) Fernando Caldeira. 2010. Boron in Timber Preservation A Riview in Its Physico-Chemical Aspects. Silva Lusitana 18(2): 179-196. 2010. UISPFL-INIA. Oeiras. Portugal
- (9) Handayani Sri. Pengujian Sifat Mekanik Bambu (Metode Pengawetan dengan Boraks). 2007. Jurnal JTSP Volume. 9, No. 1
- (10) Salmayanti. 2013. Pengaruh Konsentrasi dan Lama Perendaman Bahan Pengawet Daun Tembelekan (*Lantana camara* L.) pada Kayu Bayur (*Pterospermum* sp) Terhadap Serangan Rayap Tanah (*Coptotermes* sp). Warta Rimba. Vol. 1, No. 1, Hal 1-8.
- (11) Tenrirawe, A & MS. Pabbage. 2007. Pengendalian Penggerek Batang Jagung (*Ostrinia furnacalis* G.) Dengan Ekstrak Daun Sirsak (*Annona muricata* L.). Prosiding Seminar Ilmiah dan Pertemuan Tahunan PEI dan PFI XVIII Komda Sul-Sel. Balai Penelitian Tanaman Sereal, Maros
- (12) Grainge, M.S. and M.R. Ahmed. 1989. Hand Books of Plant with Pest Control Properties. John Wiley and Son. New York.
- (13) Hadi, M., J.W. Hidayat, K. Baskoro. 2000. Uji Potensi Ekstrak Daun Eupatorium, odoratum sebagai Bahan Insektisida Alternatif Toksisitas dan Efek Antimakan Terhadap Larva *Heliothis armigera* Hubner. Jurnal Sains dan Matematika. Fakultas MIPA Undip. Semarang
- (14) Simanjuntak. 2007. Efektifitas Tepung Daun Sirsak Untuk Mengendalikan Kumbang Bubuk Kacang Pada Biji Kacang Hijau. Sukorharjo : Fakultas Pertanian Universitas Veteran Bangun Nusantara
- (15) Yos Wahyu Harinta. 2013. Efektifitas Tepung Daun Sirsak (*Annona muricata*) Untuk Mengendalikan Kumbang Bubuk Kedelai (*Callosobruchus analis* F.) Pada Biji Kedelai (*Glycine Max* L.). Fakultas Pertanian. Universitas Veteran Bangun Nusantara.
- (16) SNI 03-6847-2002. Metode Pengujian Berat Jenis Kayu dan Bahan Dari Kayu Dengan Cara Pencelupan Dalam Air. PUSLITBANG-Badan Standarisasi Nasional.
- (17) SNI 03-6850-2002. Metode Pengujian Pengukuran Kadar Air Kayu dan Bahan Berkayu. PUSLITBANG-Badan Standarisasi Nasional.
- (18) SNI 01-7207-2006. Uji Ketahanan Kayu dan Produk Kayu Terhadap Organisme Perusak Kayu. PUSLITBANG-Badan Standarisasi Nasional.

PRESERVATION OF DURIAN TIMBER AND COCONUT TIMBER WITH SOURSOP LEAF EXTRACT

ORIGINALITY REPORT

5%

SIMILARITY INDEX

3%

INTERNET SOURCES

3%

PUBLICATIONS

1%

STUDENT PAPERS

PRIMARY SOURCES

- | | | |
|--------------------------------------------------------------------------------------------------------------------------------------------------------------|---------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|---------------------------------------------------------------------------------------------------------------------------------------------------------------|
| <div style="background-color: #f08080; width: 40px; height: 40px; display: flex; align-items: center; justify-content: center; margin-bottom: 10px;">1</div> | <p>Hadi, Y. S., M. Y. Massijaya, D. Hermawan, and A. Arinana. "Feeding rate of termites in wood treated with borax, acetylation, polystyrene, and smoke", Journal of the Indian Academy of Wood Science, 2015.</p> <p>Publication</p> | <div style="background-color: #f08080; width: 40px; height: 40px; display: flex; align-items: center; justify-content: center; margin-bottom: 10px;">1%</div> |
| <div style="background-color: #f080f0; width: 40px; height: 40px; display: flex; align-items: center; justify-content: center; margin-bottom: 10px;">2</div> | <p>www.scielo.org.mx</p> <p>Internet Source</p> | <div style="background-color: #f080f0; width: 40px; height: 40px; display: flex; align-items: center; justify-content: center; margin-bottom: 10px;">1%</div> |
| <div style="background-color: #8080ff; width: 40px; height: 40px; display: flex; align-items: center; justify-content: center; margin-bottom: 10px;">3</div> | <p>alternativeenvironments.com</p> <p>Internet Source</p> | <div style="background-color: #8080ff; width: 40px; height: 40px; display: flex; align-items: center; justify-content: center; margin-bottom: 10px;">1%</div> |
| <div style="background-color: #80bfff; width: 40px; height: 40px; display: flex; align-items: center; justify-content: center; margin-bottom: 10px;">4</div> | <p>Rini Kusumawardani, Rizki Kurniadhi, Muhammad Mukhlisin, Djoko Legono. "Rainfall threshold for triggering debris flow on Merapi volcano area, Yogyakarta, Indonesia", AIP Publishing, 2017</p> <p>Publication</p> | <div style="background-color: #80bfff; width: 40px; height: 40px; display: flex; align-items: center; justify-content: center; margin-bottom: 10px;">1%</div> |
| <div style="background-color: #80c080; width: 40px; height: 40px; display: flex; align-items: center; justify-content: center; margin-bottom: 10px;">5</div> | <p>eprints.undip.ac.id</p> <p>Internet Source</p> | <div style="background-color: #80c080; width: 40px; height: 40px; display: flex; align-items: center; justify-content: center; margin-bottom: 10px;">1%</div> |

Agung Wahyu Soesilo, Poppy Arisandy, Indah

6

Anita Sari, Rudi Harimurti. "Relationship Analysis Between Leaf-Stomata Characteristics with Cocoa Resistance to Vascular-Streak Dieback", Pelita Perkebunan (a Coffee and Cocoa Research Journal), 2016

Publication

<1%

7

A H Iswanto, T Sucipto, S S D Nadeak, W Fatriasari. "Post-treatment Effect of Particleboard on Dimensional Stability and Durability Properties of Particleboard Made From Sorghum Bagasse", IOP Conference Series: Materials Science and Engineering, 2017

Publication

<1%

8

fr.scribd.com

Internet Source

<1%

Exclude quotes Off

Exclude matches Off

Exclude bibliography On