

Growth Of A-Axis-Oriented Al-Doped ZnO Thin Film On Glass Substrate Using Unbalanced DC Magnetron Sputtering

by Sugianto Fisika

Submission date: 12-Apr-2023 08:08AM (UTC+0700)

Submission ID: 2062066381

File name: 37._Growth_of_a-axis-oriented_Al-doped_ZnO_thin_film.pdf (658.02K)

Word count: 3332

Character count: 16425

PAPER · OPEN ACCESS

Growth of *a*-axis-oriented Al-doped ZnO thin film on glass substrate using unbalanced DC magnetron sputtering

31

To cite this article: D Aryanto *et al* 2019 *J. Phys.: Conf. Ser.* **1191** 012031

8

View the [article online](#) for updates and enhancements.

You may also like

- [Improved Gas Sensing Performance of ALD AZO 3-D Coated ZnO Nanorods](#)
P. Lin, X. Chen, K. Zhang et al.

- [High-density plasma etching characteristics of aluminum-doped zinc oxide thin films in Cl₂/Ar plasma](#)
Liting Zhang, Young-Hee Joo, Doo-Seung Um et al.

39
- [Tunable physical properties of Al-doped ZnO thin films by O₂ and Ar plasma treatments](#)
Young-Hee Joo, Doo-Seung Um and Chang-Il Kim



244th Electrochemical Society Meeting

October 8 – 12, 2023 • Gothenburg, Sweden

50 symposia in electrochemistry & solid state science

▶ Deadline Extended!
Last chance to submit!

New deadline:
April 21
submit your abstract!

Growth of *a*-axis-oriented Al-doped ZnO thin film on glass substrate using unbalanced DC magnetron sputtering

D Aryanto^{1,*}, P Marwoto², T Sudiro¹, A S Wismogroho¹ and Sugianto²

¹ Research Center for Physics, Indonesian Institute of Sciences, Setu, Tangerang Selatan 15314, Banten, Indonesia

² Physics Department, Faculty of Mathematics and Science, Universitas Negeri Semarang, Gunungpati, Semarang 50229, Jawa Tengah, Indonesia

*E-mail: didi027@lipi.go.id

Abstract. Al-doped ZnO (AZO) thin films have been deposited on glass substrates using home-made DC magnetron sputtering at room temperature. The effects of Al-doping and sputtering power on the morphology and structure of AZO thin films were studied. X-ray diffraction shows that all AZO thin films have a polycrystalline nature with a hexagonal wurtzite structure. The preferential orientation planes of (100) and (110) AZO thin films were obtained by adding 2 at% Al-doping and prepared using plasma powers of 30 and 40 Watts. Texture coefficient (*TC*), crystalline size (*D*), lattice strain (ϵ), and lattice constant of the (100) and (110) planes of AZO thin film were calculated. Increasing the plasma power leads to the enhancement of crystal quality, crystalline size and grain size of *a*-axis orientation. Atomic force microscopy analysis shows that the surface of AZO thin film becomes smoother with increasing the grain size. The growth parameters in the deposition of thin films using sputtering technique have significant effect on morphology and structure of the films.

28

1. Introduction

Aluminium-doped zinc oxide (AZO) thin film is one of ZnO-based materials that has hexagonal wurtzite structure with a wide direct band gap [1]. The AZO thin film has high electrical resistivity and transparency in visible and infrared wavelength [2, 3]. In addition, AZO thin film has high chemical stability, high mechanical stability, and non-toxic and the raw materials are available in abundance [4]. These characteristics are suitable for applications in optoelectronic devices such as light-emitting diodes, flat panel displays, and thin-film solar cells [5]. Many deposition techniques have been used to fabricate AZO thin films, including sol-gel technique [6], spray pyrolysis [7], sputtering [4], pulsed laser deposition (PLD) [8], and metal organic chemical vapour deposition (MOCVD) [9]. Generally, AZO thin films are grown in polar (*c*-axis oriented) and non-polar (*a*-axis oriented) planes [10]. Mostly, however, all works reported the formation of AZO thin films with *c*-axis orientation due to the fact that the material with wurtzite structure has a high growth rate along the *c*-axis.

In the fabrication of light-emitting devices based on ZnO thin films, the *c*-axis-oriented ZnO thin films on the variety of substrates and heterostructures were grown using *c*-axis-oriented ZnO active layer. It generated the spatial separation of electrons and holes in the active layer, causing a reduction in quantum efficiency [10]. Waltereit et al. [11] reported that non-polar layer surface in the light



emitting device structures can improve quantum efficiency. Therefore, many works were carried out to fabricate ZnO thin film with a non-polar orientation, which is expected to increase the ultraviolet light emitting efficiency for ZnO-based heterostructures.

Growth of *a*-axis-oriented ZnO thin film has already been demonstrated using various techniques, such as spray pyrolysis [12], sol gel methods [10], PLD [13], metal organic aerosol deposition [14], single-source chemical vapour deposition (SSCVD) [15], and RF magnetron sputtering [16]. In this paper, we report the deposition and characterization of preferential *a*-axis-oriented polycrystalline AZO thin films on glass substrate by unbalanced DC magnetron sputtering which has not been studied.

2. Experimental Methods

The AZO thin films were deposited on glass substrates using unbalanced DC magnetron sputtering. AZO target was made from high purity ZnO powder (99.999%) doped with desired amount of high purity Al₂O₃ powder (99.999%). The amount of Al₂O₃ added to the ZnO was 1 to 2 at%. Prior to the deposition, the glass substrate was cleaned in an ultrasonic bath with acetone, methanol, and deionized water. After that, substrate was dried using O₂ gun and mounted in the sputtering chamber. Before the deposition, the target was pre-sputtered for about 10 minutes to remove contaminants from the surface. The chamber was initially evacuated to a base pressure of 1×10^{-4} Torr and the deposition was carried out at a working pressure of 4×10^{-1} Torr. The sputtering was carried out at room temperature with high-purity (99.999%) Ar gas as a plasma source. The plasma power was used in the range of 30 to 40 Watts. The distance between target and substrate was kept constant at 45 mm. X-ray diffraction (XRD) and atomic force microscopy (AFM) were used to analyze the structural properties and surface morphology of AZO thin films. The crystalline quality, preferred orientation, and surface morphology of AZO thin films were clarified and discussed.

3. Results and Discussion

The XRD patterns of undoped and Al-doped ZnO thin film recorded in the range of 30-60° are shown in Figure 1. The result shows that all films have a polycrystalline with a wurtzite-type hexagonal structure. No phases related to Al, Al₂O₃, or other impurity phases were found in the AZO thin films within the XRD detection limits. This indicates that Al³⁺ substituted the Zn²⁺ sites or incorporated into interstitial sites of ZnO lattice [17]. As seen in figure 1, the undoped ZnO thin film has a high preferential orientation along the (002) plane. Other diffraction peaks, (100) and (110), with weak intensity were also observed. This indicates that the undoped ZnO thin film exhibits a strong *c*-axis orientation perpendicular to the substrate [18]. The intensity of the (002) diffraction peak decreases and the full width at half maximum (FWHM) of the peak increases at the doped ZnO thin film with 1 at% Al. It suggests that the crystallinity of thin film is deteriorated. Ion Al³⁺ reduces the concentration of the zinc interstitial [19], resulting in suppression of the ZnO grain growth and degradation of the crystal quality. In addition, the intensity of (101) peak appears on the ZnO thin films doped with 1 at% Al. This indicates that some grains grow in other orientations besides the *c*-axis orientation [20]. The significant results are shown in the ZnO thin film with 2 at% Al doping that the intensity peaks of (100) and (110) planes increase and the diffraction peak of (002) plane is not observed. This confirms the improvement of crystal quality of *a*-axis orientation owing to the decrease in the corresponding of FWHM (as shown in figure 1). This result also shows that the grain of thin films grew parallel to the substrate surface. The Al doping causes the decrease in the degree of crystallinity of ZnO thin films [21]. The increase of Al dopant concentration is the reason for a complete change of the preferential orientation of the grains. In the sputtering technique, the crystal orientation of the interfacial grain is less dependent on the growth parameters.

Previous study shows that the intensity ratio of thin films indicates the preferential growth of the films in a particular plane [17]. According to the literature, the preferred orientation of (*h k l*) plane can be defined as a texture coefficient (*TC*) (*h k l*), which is calculated using the following formula [12]

$$TC(hkl) = \left(\frac{I_{(hkl)}/I_{r(hkl)}}{\left[\frac{1}{n} \sum I_{(hkl)}/I_{r(hkl)} \right]} \right) \quad (1)$$

where $I_{(hkl)}$, $I_{r(hkl)}$, and n indicate the X-ray diffraction intensities which obtained from the films, intensity of the reference diffraction pattern (ICDD-01076-0704), and considered number of diffraction peaks, respectively. The calculation results of texture coefficient for crystal planes of AZO thin films are shown in the Table 1. The higher value of the texture coefficient of ZnO and AZO thin films is obtained in different diffraction plane. This indicates that the preferred orientation of the film changes with increasing the amount of Al-doping. Rao and Santhoshkumar [12] confirm that the higher value of the texture coefficient indicates the preferred orientation of the films along the diffraction plane. The change in the preferred orientation is possible at the growth of thin film on amorphous substrate.

The nucleation and final growth orientation are believed to affect the crystal orientations. The growth orientation is developed into the crystallographic direction of the lowest surface energy. The grains became larger for the film that grows with a lower surface energy density [12]. This result confirms that the growth parameter in the sputtering system affects the crystal orientations.

The detail of the observed peak intensities from (100) and (110) planes of undoped ZnO and AZO thin films is shown in figure 1. Small shifts toward larger angles are shown on both peak positions. It suggests a decrease of the a -lattice parameters of AZO thin films. According to Bragg's Law ($n\lambda = 2d \sin\theta$), the change of lattice parameter d causes a shift of θ when λ is constant [17] and it is possible that the change relates to the strain relaxation in the films. It can be confirmed by the calculation of crystallographic parameters, such as average size of crystalline grain (D), lattice strain (ϵ), and lattice

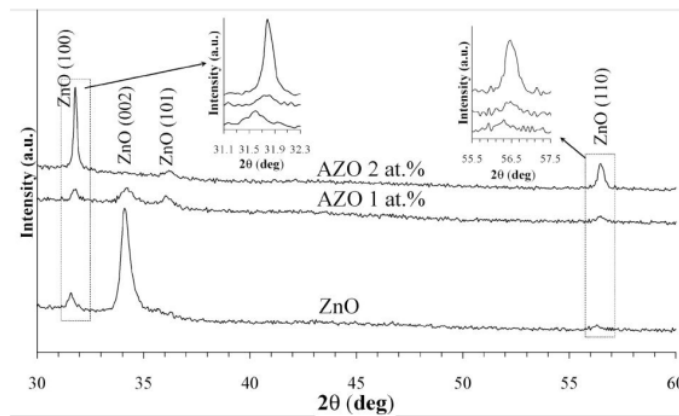


Figure 1. XRD patterns of Al-doped ZnO thin films growth at sputtering power of 30 Watt

Table 1. Texture coefficient of ZnO thin film with variation of Al-dopant.

Al-dopant	Texture coefficient (TC)			
	(100)	(002)	(101)	(110)
0	0.54	2.28	-	0.18
1%	1.22	1.73	0.56	0.49
2%	1.93	-	0.20	0.87

constant (a). The average size (D) of the crystalline grain along the a -axis was determined using Debye-Scherrer's formula [12].

$$D = \frac{0.9 \lambda}{\beta \cos \theta} \quad (2)$$

The lattice strain (ε) was calculated using the tangent formula [22]

$$\varepsilon = \frac{\beta}{(4 \tan \theta)} \quad (3)$$

The lattice parameters (a) of (100) and (110) plane were determined using the equation

$$a = \frac{\lambda}{\sqrt{3} \sin \theta} \sqrt{h^2 + hk + k^2} \quad (4)$$

where λ is the X-ray wavelength of 1.5418 Å, θ is Bragg diffraction angle of a -axis peak and β is the FWHM of θ . The crystallographic parameters of AZO thin films growth at sputtering power of 30 Watt are calculated according to (100) and (110) planes and tabulated in Table 2. It is observed that the lattice parameter (a) of AZO thin films decreases compared to the ZnO thin film. These results confirm that the shifted angles are affected by a -lattice parameters. The replacement of Zn^{2+} ions by Al^{3+} ions also contributes to that case due to the different in radius of Zn^{2+} ions (0.0740 nm) and Al^{3+} ions (0.0535 nm) [17]. However, the addition of Al doping also influences the crystalline size of thin films. Compared to the ZnO thin films, the crystalline size of AZO thin films is smaller. Similar result is shown by Sahay and Nath [22] and Chen et al. [17] that the crystalline size decreases with increasing Al-doping.

Figure 2 shows the XRD patterns of ZnO and AZO thin films at the sputtering power of 40 Watt. It can be seen that two dominant peaks are observed in XRD pattern corresponding to (100) and (110) planes. This result indicates that the film has a polycrystalline hexagonal wurtzite structure with a -axis orientation. The crystallographic parameters of AZO thin films growth at sputtering power of 40 Watt are calculated and tabulated in Table 3. However, calculation of texture coefficient shows that the preferred orientation of ZnO and AZO (2 at% Al) thin films changes from (100) to (110) planes compared to ZnO and AZO (2 at% Al) at the plasma power of 30 Watt. In this case, the increase of sputtering power from 30 to 40 Watt influences the dominant of crystal growth in the (110) plane. The intensities of the (100) and (110) diffraction peaks increase and shift to larger angle with the addition of 2 at% Al. It further suggests that the improvement in the crystallinity and the value of a -lattice parameter occur. The increase of the peak intensity is also influenced by the grain and crystalline sizes [23]. The ions or ion clusters can obtain more energy with increasing the plasma power. It causes ions or ion clusters to easily adjust their own bond direction and length, so that they obtain an optimum bonding to the adjacent atoms and this helps them to nucleate and grow. Therefore, the crystalline size of AZO (2 at% Al) thin films becomes larger with the sputtering power of 40 Watt. Table 2 and 3 also show that the a -lattice parameters decrease with the increase of plasma power. This may be due to the interstitial and substitution of Al atoms or ions in the lattice of AZO thin films [24].

Table 2. Calculated crystalline size, lattice strain, and lattice constants from (100) and (110) planes of ZnO thin film with various Al-doping.

Al-doping	($h k l$)	FWHM	D [Å]	ε [%]	a [Å]
0	(100)	0.28	5.219	0.244	3.2686
	(110)	0.30	5.246	0.140	3.2674
1%	(100)	0.35	4.123	0.307	3.2465
	(110)	0.40	3.938	0.186	3.2586
2%	(100)	0.20	7.214	0.097	3.2514
	(110)	0.33	4.750	0.154	3.2586

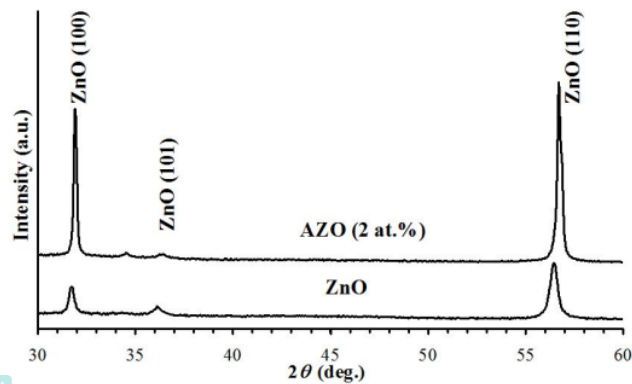


Figure 2. XRD patterns of Al-doped ZnO thin films growth at sputtering power of 40 Watt.

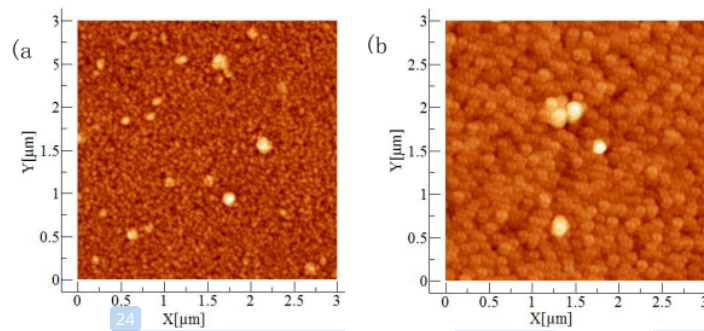


Figure 3. AFM images of AZO (2 at% Al) thin films growth with the sputtering power of (a) 30 Watt and (b) 40 Watt.

Table 3. Calculated texture coefficient, crystalline size, lattice strain, and lattice constants from (100) and (110) planes of ZnO and Al-doped ZnO (2%) thin film at the sputter power of 40 Watt.

Al-dopant	(<i>h k l</i>)	TC	FWHM	<i>D</i> [Å]	ε [%]	<i>A</i> [Å]
0	(100)	0.50	0.30	4.809	0.264	3.2520
	(110)	1.49	0.44	3.580	0.205	3.2586
2%	(100)	0.65	0.22	6.527	0.194	3.2410
	(110)	1.34	0.28	5.705	0.128	3.2469

Figure 3 shows the AFM images of AZO (2 at% Al) at plasma power of 30 and 40 Watts. It can be seen that the film grows with granular grain. The surface morphology of the AZO (2 at% Al) thin films deposited at 30 Watt shows a coarse surface with non-uniform in grain size. The grain size of the AZO (2 at% Al) thin films becomes larger, dense, and uniform in size when the plasma power was increased to 40 Watt. The root mean square (RMS) of roughness for plasma power of 30 and 40 Watts of AZO thin film was 8.546 and 6.999 nm, respectively. This indicates the enhancement in the migration of sputtered atoms on the thin films surface during the growth and the surface roughness reduction. Another reason why the RMS roughness reduces is due to the energy of particles arriving at

the surface increases with increasing plasma power, leaving more energy for surface diffusion caused by collisions with more atoms. The result of AFM analysis is in good agreement with the results of XRD analysis.

4. Conclusions

The AZO thin films have been deposited on glass substrate using unbalanced DC magnetron sputtering system with various doping concentration and plasma power. The films have polycrystalline structure with preferred orientation of (100) and (110). The crystallinity and the a-axis-oriented AZO (2 at% Al) thin films prepared at 40 Watt power plasma give better film quality compared to others sample. The doping concentration and plasma power strongly influence the growth of thin film as well as structure and morphology of the films.

Acknowledgments

This work was supported Ministry of Research, Technology and Higher Education, Indonesia under Grant No. 013/P/RPL-LIPI/INSINAS-2/VII/2018 and 158/P/RPL-LIPI/INSINAS-1/III/2018. The authors are grateful to Laboratory of Thin Film, Physics Department, Universitas Negeri Semarang and Research Center for Physics-LIPI for providing the research facilities.

References

- [1] Jeong S H, Park B N, Yoo D G and Boo J H 2007 *J. Korean Phys. Soc.* **50** 622
- [2] Chandramohan R, Vijayan T A, Arumugam S, Ramalingam H B, Dhanasekaran V, Sundaram K and Mahalingam T 2011 *Mater. Sci. Eng. B* **176** 152
- [3] Kodu M, Arroval T, Avarmaa T, Jaaniso R, Kink I, Leinberg S, Savi K and Timusk M 2014 *Appl. Surf. Sci.* **320** 756
- [4] Liu C, Xu Z, Zhang Y, Fu J, Zang S and Zuo Y 2015 *Mater. Lett.* **139** 279
- [5] Eshaghi A and Hajkarimi M 2014 *Optik* **125** 5746
- [6] Mahroug A, Boudjadar S, Hamrit S and Guerbous L 2014 *Mater Lett* **134** 248
- [7] Gahtar A, Rahal A, Benhaoua B and Benramache S 2014 *Optik* **125** 3674
- [8] Taabouche A, Bouabellou A, Kermiche F, Hanini F, Sedrati C, Bouachiba Y and Benazzouz C 2016 *Ceram. Int.* **42** 6701
- [9] Su J, Tang C, Niu Q, Zang C, Zhang Y and Fu Z 2012 *Appl. Surf. Sci.* **258** 8595
- [10] Bhole M P and Patil D S 2007 *Optoelectron. Adv. Mater.* **1** 672
- [11] Waltereit P, Brandt O, Ramsteiner M, Trampert A, Grahn H T, Menniger J, Reiche M and Ploog K H 2001 *J. Cryst. Growth* **227-228** 437
- [12] Rao T P and Santhoshkumar M C 2009 *Appl. Surf. Sci.* **255** 7212
- [13] Nistor L C, Ghica C, Matei D, Dinescu G, Dinescu M and Tendeloo G V 2005 *J. Cryst. Growth* **277** 26.
- [14] Neumann U, Grunwald R, Griebner U and Steinmeyer G 2005 *Appl. Phys. Lett.* **87** 171108-1
- [15] Dai L P, Deng H, Chen G, Teng C F, Wei M and Li Y 2007 *Vacuum* **81** 969
- [16] You J B, Zhang X W, Cai P F, Dong J J, Gao Y, Yin Z G, Chen N F, Wang R Z and Yan H 2009 *Appl. Phys. Lett.* **94** 262105-1
- [17] Chen J, Chen D, He J, Zhang S and Chen Z 2009 *Appl. Surf. Sci.* **255** 9413
- [18] Zhao L, Shao G-J, Qina X-J and Han S-H-Z 2011 *J. Alloys Compd.* **509** L297
- [19] Wang M, Lee K E, Hahn S H, Kim E J, Kim S, Chung J S, Shin E W and Park C 2007 *Mater. Lett.* **61** 1118
- [20] Li J, Xu J, Xu Q and Fang G 2012 *J. Alloys Compd.* **542** 151
- [21] Sandeep K M, Bhat S and Dharmaprasadh S M 2017 *J. Phys. Chem. Solids* **104** 36.
- [22] Sahay P P and Nath R K 2008 *Sens. Actuators B-Chem.* **134** 654
- [23] Purohit A, Chander S, Sharma A, Nehra S P and Dhaka M S 2015 *Opt. Mater.* **49** 51
- [24] Kuo S-Y, Liu K-C, Lai F-I, Yang J-F, Chen W-C, Hsieh M-Y, Lin H-I and Lin W-T, *Microelectron. Reliab.* **50** 730

Growth Of A-Axis-Oriented Al-Doped ZnO Thin Film On Glass Substrate Using Unbalanced DC Magnetron Sputtering

ORIGINALITY REPORT

16%

SIMILARITY INDEX

5%

INTERNET SOURCES

14%

PUBLICATIONS

4%

STUDENT PAPERS

PRIMARY SOURCES

- 1 Liszulfah Roza, Vivi Fauzia, Mohd. Yusri Abd Rahman. "Tailoring the active surface sites of ZnO nanorods on the glass substrate for photocatalytic activity enhancement", *Surfaces and Interfaces*, 2019
Publication 1%
- 2 Submitted to University of Mustansiriyah
Student Paper 1%
- 3 electrochemsci.org
Internet Source 1%
- 4 www.ias.ac.in
Internet Source 1%
- 5 www.science.gov
Internet Source 1%
- 6 Wook Shin, S.. "Effect of a ZnO buffer layer on the properties of Ga-doped ZnO thin films grown on Al₂O₃ (0001) substrates at a low growth temperature of 250°C", *Journal of Crystal Growth*, 20100415
Publication 1%

7 Gaurav Saraf, Jian Zhong, Olga Dulub, Ulrike Diebold, Theo Siegrist, Yicheng Lu. "Surface and Interface Properties of Metal-Organic Chemical Vapor Deposition Grown a-Plane Mg x Zn1-x O (0≤x≤0.3) Films", Journal of Electronic Materials, 2007

Publication

8 Grzegorz Muziol, Mateusz Hajdel, Marcin Siekacz, Henryk Turski et al. "III-nitride optoelectronic devices containing wide quantum wells - unexpectedly efficient light sources", Japanese Journal of Applied Physics, 2021

Publication

9 Jufriadi, Bakri, Agus Geter E. Sutjipto, R. Othman, and R. Muhida. "Microstructure and Electrical Properties of AZO Films Prepared by RF Magnetron Sputtering", Advanced Materials Research, 2011.

Publication

10 Lee, J.. "Structural, electrical and optical properties of ZnO:Al films deposited on flexible organic substrates for solar cell applications", Thin Solid Films, 20070531

Publication

11 Submitted to Multimedia University

Student Paper

12	dokumen.tips Internet Source	1 %
13	Lai, F.. "Ultra-thin Cr ² O ³ well-crystallized films for high transmittance APSM in ArF line", <i>Microelectronic Engineering</i> , 200306 Publication	<1 %
14	Submitted to National Institute of Technology, Kurukshetra Student Paper	<1 %
15	Submitted to National Chung Hsing University Student Paper	<1 %
16	Submitted to UIN Maulana Malik Ibrahim Malang Student Paper	<1 %
17	Submitted to Universiti Malaysia Pahang Student Paper	<1 %
18	ir.nctu.edu.tw Internet Source	<1 %
19	Castaneda, L.. "Formation of indium-doped zinc oxide thin films using chemical spray techniques: The importance of acetic acid content in the aerosol solution and the substrate temperature for enhancing electrical transport", <i>Thin Solid Films</i> , 20060501 Publication	<1 %

20 D Yuvaraj. "Room temperature synthesis of ZnO nanoneedles by activated reactive evaporation", Journal of Physics D Applied Physics, 02/07/2009 $<1\%$
Publication

21 Fu, R.K.. "Molybdenum-carbon film fabricated using metal cathodic arc and acetylene dual plasma deposition", Surface & Coatings Technology, 20040802 $<1\%$
Publication

22 Submitted to Savitribai Phule Pune University $<1\%$
Student Paper

23 Shimul Kanti Nath, Nishita Chowdhury, Md. Abdul Gafur. "Effect of Co Doping on Crystallographic and Optoelectronic Properties of ZnO Thin Films", Journal of Superconductivity and Novel Magnetism, 2014 $<1\%$
Publication

24 S. Hosseinabadi, F. Abrinaei, M. Shirazi. "Statistical and fractal features of nanocrystalline AZO thin films", Physica A: Statistical Mechanics and its Applications, 2017 $<1\%$
Publication

25 Chawalit Bhoomanee, Pipat Ruankhama, Supab Choopun, Aschariya Prathan, $<1\%$

Duangmanee Wongratanaphisan. "Effect of Al-doped ZnO for Electron Transporting Layer in Planar Perovskite solar cells", Materials Today: Proceedings, 2019

Publication

26

El Manouni, A.. "Effect of thermal annealing on ZnO:Al thin films grown by spray pyrolysis", Superlattices and Microstructures, 200707

Publication

27

Foo, K.L., U. Hashim, Chun Hong Voon, and M. Kashif. "Fabrication and Characterization of ZnO Thin Films by Sol-Gel Spin Coating Method for pH Measurement", Advanced Materials Research, 2015.

Publication

28

Guillen, C.. "Transparent and conductive ZnO:Al thin films grown by pulsed magnetron sputtering in current or voltage regulation modes", Vacuum, 20080219

Publication

29

Janne-Petteri Niemelä, Giovanni Marin, Maarit Karppinen. "Titanium dioxide thin films by atomic layer deposition: a review", Semiconductor Science and Technology, 2017

Publication

30

Kun-Yang Wu. "Preparation and conductivity enhancement of Al-doped zinc oxide thin

<1 %

<1 %

<1 %

<1 %

<1 %

films containing trace Ag nanoparticles by the sol-gel process", Nanotechnology, 08/01/2007

Publication

31

L C Nistor, C Ghica, V Kuncser, D Pantelica, J-J Grob, G Epurescu, M Dinescu.

"Microstructure-related magnetic properties in Co-implanted ZnO thin films", Journal of Physics D: Applied Physics, 2013

Publication

32

Mass, J.. "Effect of high substrate temperature on Al-doped ZnO thin films grown by pulsed laser deposition", Materials Science & Engineering B, 20030925

Publication

33

Rajendra Salim, Swastya Rahastama, Adi Wijayanto, Fadli Robiandi, Musyarofah.

"Dosimetry and defect analysis of aluminum-doped zinc oxide after irradiation with $^{90}\text{Sr}/^{90}\text{Y}$ ", Applied Radiation and Isotopes, 2023

Publication

34

Rayees Ahmad Zargar, Peerzada Ajaz Ahmad, Muzafer Ahmad Sheer Gogre, Malik Mubasher Hassan. "Screen printing coating of $(\text{ZnO})_{0.8}(\text{CdO})_{0.2}$ material for optoelectronic applications", Optical and Quantum Electronics, 2020

Publication

<1 %

<1 %

<1 %

<1 %

35

d-nb.info

Internet Source

<1 %

36

nopr.niscpr.res.in

Internet Source

<1 %

37

soar-ir.repo.nii.ac.jp

Internet Source

<1 %

38

Ehsan M. Aghkonbad, Hassan Sedghi, Maryam M. Aghgonbad. "Optical Characterization of Al-doped ZnO Films via Sol-gel Method Using Spectroscopic Ellipsometry", Nanoscience & Nanotechnology-Asia, 2020

Publication

<1 %

39

K. Prabakar, Choongmo Kim, Chongmu Lee. "UV, violet and blue-green luminescence from RF sputter deposited ZnO:Al thin films", Crystal Research and Technology, 2005

Publication

<1 %

40

Liu, Wei-Sheng, Wei-Ku Chen, Shen-Yu Wu, and Kuang-Po Hsueh. "Improved Crystal Quality of Transparent Conductive Ga-doped ZnO Films by Magnesium Doping Through Radio-Frequency Magnetron Sputtering Preparation", Journal of the American Ceramic Society, 2014.

Publication

<1 %

41

Sung-Hae Lee, Se-Hoon Han, Hyun Suk Jung, Hyunjung Shin et al. "Al-Doped ZnO Thin Film: A New Transparent Conducting Layer for ZnO Nanowire-Based Dye-Sensitized Solar Cells", The Journal of Physical Chemistry C, 2010

Publication

<1 %

42

Tomasz Tański, Marta Zaborowska, Paweł Jarka, Anna Woźniak. "Hydrophilic ZnO thin films doped with ytterbium and europium oxide", Scientific Reports, 2022

Publication

<1 %

43

Seren Nar, Ömer Şahin, Sabit Horoz. "Fabrication of Pure Sb₂S₃ and Fe (2.5%): Sb₂S₃ Thin Films and Investigation Their Properties", Journal of Inorganic and Organometallic Polymers and Materials, 2019

Publication

<1 %

Exclude quotes On

Exclude matches < 5 words

Exclude bibliography On

Growth Of A-Axis-Oriented Al-Doped ZnO Thin Film On Glass Substrate Using Unbalanced DC Magnetron Sputtering

GRADEMARK REPORT

FINAL GRADE

/0

GENERAL COMMENTS

Instructor

PAGE 1

PAGE 2

PAGE 3

PAGE 4

PAGE 5

PAGE 6

PAGE 7
