

# Conversion of Free Fatty Acid in Calophyllum inophyllum Oil to Fatty Acid Ester as Precursor of Bio-Based Epoxy Plasticizer via SnCl<sub>2</sub>-Catalyzed Esterification

*by Ratna Kusumaningtyas*

---

**Submission date:** 18-Apr-2023 09:40AM (UTC+0700)

**Submission ID:** 2067897793

**File name:** polymers-15-00123\_1.pdf (2.51M)

**Word count:** 8705

**Character count:** 48692

# Conversion of Free Fatty Acid in *Calophyllum inophyllum* Oil to Fatty Acid Ester as Precursor of Bio-Based Epoxy Plasticizer via $\text{SnCl}_2$ -Catalyzed Esterification

Ratna Dewi Kusumaningtyas <sup>\*</sup>, Haniif Prasetiawan, Nanda Dwi Anggraeni, Elva Dianis Novi Anisa and Dhoni Hartanto

Chemical Engineering Department, Faculty of Engineering, Universitas Negeri Semarang, Sekaran, Gunungpati, Semarang 50229, Indonesia

\* Correspondence: ratnadewi.kusumaningtyas@mail.unnes.ac.id

**Abstract:** The preparation and application of bio based plasticizers derived from vegetable oils has gained increasing attention in the polymer industry to date due to the emerging risk shown by the traditional petroleum-based phthalate plasticizer. Epoxy fatty acid ester is among the prospective alternative plasticizers since it is ecofriendly, non-toxic, biodegradable, low migration, and low carbon footprint. Epoxy plasticizer can be synthesized by the epoxidation reaction of fatty acid ester. In this study, the preparation of fatty acid ester as a green precursor of epoxy ester plasticizer was performed via esterification of free fatty acid (FFA) in high acidic *Calophyllum inophyllum* Seed Oil (CSO) using methanol in the presence of  $\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$  catalyst. The analysis of the process variables and responses using Box–Behnken Design (BBD) of Response Surface Methodology (RSM) was also accomplished. It was found that the quadratic model is the most appropriate model for the optimization process. The BBD analysis demonstrated that the optimum FFA conversion and residual FFA content were 75.03% and 4.59%, respectively, achieved at the following process condition: a reaction temperature of 59.36 °C, a reaction time of 117.80 min, and a catalyst concentration of 5.61%. The fatty acid ester generated was an intermediate product which can undergo a further epoxidation process to produce epoxy plasticizer in polymeric material production.

**Keywords:** *Calophyllum inophyllum* seed oil;  $\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$ ; fatty acid ester; response surface methodology; epoxy plasticizer



**Citation:** Kusumaningtyas, R.D.; Prasetiawan, H.; Anggraeni, N.D.; Anisa, E.D.N.; Hartanto, D. Conversion of Free Fatty Acid in *Calophyllum inophyllum* Oil to Fatty Acid Ester as Precursor of Bio-Based Epoxy Plasticizer via  $\text{SnCl}_2$ -Catalyzed Esterification. *Polymers* **2023**, *15*, 123. <https://doi.org/10.3390/polym15010123>

Academic Editor: Chengji Zhao

Received: 29 November 2022

Revised: 13 December 2022

Accepted: 15 December 2022

Published: 28 December 2022



**Copyright:** © 2022 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

## 1. Introduction

Plasticizer is an important additive in polymer, especially in the plastic industry. The IUPAC definition of plasticizer is a substance included in a material such as plastic or elastomer to enhance its flexibility, working ability, and distensibility. This function can be executed by decreasing the second order transition temperature, also known as the glass transition temperature [1]. Plasticizers are low molecular weight molecules sited between the polymer chains that develop a secondary bond with the polymer chains. Thus, they interrupt the hydrogen bond and spread the polymer chains apart, which improves the polymer properties in ways such as lowering the modulus, making the mass character of the material softer, providing better gas permeability, enhancing the degree of crystallinity, and reducing the tension of deformation [2,3]. The demand for plasticizer has notably increased along with the rapid growth of the plastic and polymer industry during the last decade.

To date, the most widely used plasticizers are conventional petroleum-based phthalates, i.e., diisononyl phthalate (DINP), di(2-ethylhexyl) phthalate (DEHP), dibutyl phthalate (DBP), diethyl phthalate (DEP), di-isobutyl phthalate (DIBP), and n-butyl benzyl phthalate (BBP). Phthalates are applied in many polymer products, especially PVC products. However, utilization of phthalate plasticizers has caused problems recently, since they

exhibit a negative effect on human health and the environment [4–7]. Besides, they do not have biodegradable and renewable characteristic. Therefore, it is essential to develop a non-toxic, biodegradable, and renewable plasticizer with good performance which can be used in various polymer products, such as food packaging, consumer goods, electrical insulation, and medical products.

Bio based plasticizers derived from vegetable oils are among the prospective alternative since they have ecofriendly, non-toxic, biodegradable, low migration, and low carbon footprint properties. Various types of bio-plasticizers can be produced from vegetable oil raw materials such as, for instance, epoxidized oil (triglyceride) and epoxidized fatty acid esters [1,6,8]. Among numerous bio based plasticizers, epoxidized fatty acid methyl ester, also known as epoxy fatty acid ester, is favorable for application as an additive material in PVC, which is attributable to its benefits, viz., high plasticizing efficiency, renewability, biodegradability, and cost-effectiveness [9]. Epoxy fatty acid esters have better solubility in the polymeric matrix than epoxidized oil and offer superior elasticity even at low temperatures [10].

Vegetable oil fatty acid esters as precursor of epoxy fatty acid esters can be prepared via two different routes, namely the transesterification of triglyceride and the esterification of free fatty acid. Vegetable oils are mainly composed of triglycerides, which consist of fatty acid units linked to glycerol [11]. Fatty acid esters can be synthesized by transesterification of the triglyceride in the oil using a short chain alcohol such as methanol over an acid or base catalyst [9,12,13]. The nonedible vegetable oils, however, generally contain high free fatty acid (FFA) in addition to the main triglyceride compound. The high FFA content causes the acidic character of the vegetable oil. FFA is usually unfavorable since it has bad odor and makes the oil rancid [14]. The standard quality of commercial vegetable oil such as crude palm oil is required to have an FFA content lower than 5% [15]. In spite of this fact, FFA can be transformed to fatty acid ester via an esterification reaction using short chain alcohols in the presence of an acid catalyst [13,16]. Fatty acid esters synthesized via either triglyceride transesterification or FFA esterification can further undergo an epoxidation reaction to produce epoxy fatty acid esters. Fatty acid esters have a low viscosity; hence they need lower organic solvent in the epoxidation reaction [17].

The epoxidation reaction requires fatty acid ester precursors which comprise a high content of unsaturated fatty esters [10,17]. Epoxidation is a double bond addition reaction, in which the double bonds are transformed into oxirane [7]. Thus, it involves the formation of oxirane (epoxy) through the reaction between the olefinic double bond compound and the peroxyacids or peracids. Epoxides or oxiranes consist of cyclic ethers with a reactive 3-membered ring. Peroxyacids in the epoxidation reaction are generally yielded via the reaction between acetic acid or formic acid with hydrogen peroxide using a strong inorganic acid. It can be also conducted by directly introducing peroxyacid into the reactants mixture. The resulting peroxyacids then convert the double bond into the epoxy. A recent innovation in the area of fatty acid esters conversion to epoxy is enzymatic reaction technology [18,19].

Several works related to the epoxidation of fatty acid esters sourced from various vegetable oils, such as soybean, linseed, rapeseed, castor, grapeseed, avocado, olive, microalgae, RBD palm olein, and sunflower oils [9,17,18,20–22] have been extensively reported. However, the synthesis of an epoxy fatty acid ester derived from *Calophyllum inophyllum* Seed Oil has not been broadly studied. *Calophyllum inophyllum* Seed Oil (CSO) is a prospective source of fatty acid esters as precursors of epoxy fatty acid esters. The *Calophyllum inophyllum* plant, locally known as the nyamplung or tamanu tree or beach mahogany, originally comes from Indo-Pacific area (Africa, India, South East Asia, Australia, and Pacific islands) [23]. The *Calophyllum inophyllum* seed is an excellent source of vegetable oil with oil content of 65–75% [24]. Based on our previous investigation, *Calophyllum inophyllum* Seed Oil (CSO) comprises high unsaturated fatty acid. The fatty acids composing CSO are predominantly unsaturated fatty acids (40% oleic acid, 29.94% linoleic acid, and 0.6% arachidic acid) with small portion saturated fatty acid (15.51% palmitic acid and 14.39% stearic acid). CSO is a nonedible oil, containing gum and high FFA content of 19.18% [25]. The undesired high

FFA content in CSO has the potential to be converted to fatty acid esters as precursor of epoxy fatty acid ester plasticizer through acid catalyzed esterification using methanol.

In this work, the esterification of the FFA present in CSO with methanol using  $\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$  was carried out to produce fatty acid ester as precursor of epoxy fatty acid ester. The heterogeneous  $\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$  (tin chloride) catalyst was employed to promote the reaction by reason of its superiority.  $\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$  is a low cost Lewis acid catalyst which is tolerant to water, stable, minimally corrosive, and simple to handle. It is milder than Brønsted acid catalyst but capable of providing high catalytic activity. Lewis acids are compounds with lack of electrons which can perform to activate substrate rich in electrons [26,27]. This catalyst also possesses the general advantages of heterogeneous catalyst, specifically easy separation from the product mixture and reusability [28].

To optimize the process condition for the esterification of FFA in CSO with methanol in the presence on  $\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$ , a statistical model was applied. Response Surface Methodology (RSM) is a rigorous technique that can be implemented to assess numerous parameters with a minimum number of experiments. It involves a mathematical and statistical procedure to create an experimental design which can examine the influences of the independent process variables on the response variable, thus allowing the optimum response to be verified [29]. In the optimization process, a suitable design should be employed. The models that are applicable for the factorial analysis are Box–Behnken Design (BBD), Doehlert Design (DD) and Central Composite Design (CCD). These models can predict the response function to the actual data using the quadratic function [30]. BBD is more efficient and cost-effective than DD and CCD since it has no extreme points and needs fewer points than the others for the analysis and optimization [31]. The purpose of this work was to determine the proper process condition which results in the highest reaction conversion and the lowest residual FFA by using BBD in RSM for the esterification of FFA in CSO with methanol over  $\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$  catalyst. At the optimum process condition, the highest yield of fatty acid esters as precursor of epoxy plasticizer was also achieved.

32

## 2. Materials and Methods

### 2.1. Materials

*Calophyllum inophyllum* Seed Oil (CSO) was obtained from a local supplier in Central Java, Indonesia. It had an acid value and FFA content of 36.542 mg KOH/g oil and 18.39%, respectively. The most dominant fatty acid composing the CSO was oleic acid, which has a molecular weight of 282.52 g/mol as reported in our previous work [25]. The other materials used were phosphoric acid, methanol (technical grade, purchased from local chemical store), ethanol p.a. (Merck),  $\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$  or tin(II)chloride catalyst (Merck), KOH p.a. (Merck), oxalic acid p.a. (Merck), distilled water, and phenolphthalein solution.

### 2.2. Methods

#### 2.2.1. Esterification Reaction

Prior to the esterification reaction, the CSO was degummed using phosphoric acid to remove the phospholipids and mucilaginous gums content [32]. The acid degumming process was performed using a similar method to the previous work [25]. The degummed CSO was then underwent the esterification reaction. Initially, the CSO and methanol were weighed to obtain a molar ratio of CSO and methanol of 1:30. The CSO was heated until it reached the desired temperature (40 °C, 50 °C, and 60 °C) in a three necks flask reactor. At the same time, a certain amount of  $\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$  was solved and mixed with methanol in another flask. The  $\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$  catalyst employed for the reaction was varied at 1%, 3%, 5%, and 7% w/w of CSO. The mixture of methanol and  $\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$  catalyst was separately heated up to the similar temperature. Once the targeted temperature was attained, the methanol- $\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$  catalyst mixture was introduced into the reactor, and this was recorded as the initial time of the esterification reaction. The esterification reaction was conducted for 120 min using a batch reactor which was equipped with a condenser and magnetic stirrer. The high agitation speed of 1000 rpm was applied to enhance the mixing



of the solid catalyzed reaction [33–35]. Samples were taken periodically every 10 min. The samples were tested to determine the acid value using standard carboxylic-acid-titration techniques [36,37]. According to Kurniati et al. [38], The FFA conversion ( $X_A$ ) at a certain sampling time was determined based on the residual acid value at reaction time  $t$  as shown in Equation (1).

$$X_A = \frac{AV_i - AV_t}{AV_i} \times 100\% \quad (1)$$

where  $X_A$  is the reaction conversion (%),  $AV_i$  is the initial acid value ( $t = 0$ ) (mg), and  $AV_t$  is the residual acid value at reaction time (mg).

The FFA content was calculated using Equation (2) [39].

$$FFA \text{ Content } (\%) = \frac{A \times N \times MW}{G \times 1000} \times 100 \quad (2)$$

where FFA Content is the reaction conversion (%),  $A$  is the volume of KOH (ml),  $N$  is the normality of KOH (N),  $MW$  is the average molecular weight of the fatty acids (g/mol), and  $G$  is the sample weight (g).

### 2.2.2. Optimization Using Box–Behnken Design of Response Surface Methodology

The experimental data were used for the optimization of the operation condition to obtain the lowest FFA content in the CSO and the highest reaction conversion using Box–Behnken Design (BBD) of Response Surface Methodology (RSM). The simulation was conducted using Design Expert version 13 software. BBD was chosen since it can optimize the parameters effectively with the minimum number of experiments and allows analysis of the interactions between the parameters. In this study, BBD was performed using a total of 15 experimental runs, and the center point measurements were repeated three times to accomplish an accurate calculation of the experimental error. The parameters studied as the independent variables in this work were temperature (A), reaction time (B), and catalyst concentration (C). Each parameter was examined at 3 levels, viz.,  $-1$  indicated the low level,  $+1$  represented the high level, and  $0$  was used as the central point to evaluate the experimental error [40]. The independent variables and their levels are presented in Table 1. Furthermore, the design of the randomized response model is shown in Table 2.

The average magnitude of error between the predicted value and actual value (experimental data) was calculated using Equation (3), in which MAPE is Mean Absolute Percentage Error and  $n$  is the number of data points.

$$MAPE = \sum \frac{\left| \frac{\text{predicted value} - \text{experimental data}}{\text{experimental data}} \right|}{n} \times 100\% \quad (3)$$

**Table 1.** Independent Variables Range and Level Used in BBD Experimental Design.

Independent Variable	Factor	Coded Level		
		$-1$	$0$	$1$
Temperature (°C)	A	40	50	60
Reaction Time (min)	B	60	90	120
Catalyst Concentration (%)	C	3	5	7


**Table 2.** Design of the Randomized Response Model.

Run	Factor A Temperature (°C)	Factor B Reaction Time (min)	Factor C Catalyst Concentration (%)
1	40	120	5
2	40	60	5
3	60	90	3
4	40	90	7
5	60	90	7
6	50	120	3
7	60	120	5
8	50	60	7
9	50	90	5
10	40	90	3
11	60	60	5
12	50	60	3
13	50	90	5
14	50	120	7
15	50	90	5

### 3. Results and Discussion

#### 3.1. Effects of the Experimental Variables on the Reaction Conversion


The esterification of high acidic *Calophyllum inophyllum* seed oil (CSO) with methanol in the presence of SnCl<sub>2</sub>·2H<sub>2</sub>O catalyst to transform free fatty acid (FFA) to fatty acid ester as precursor of bio-based epoxy plasticizer has been conducted in this work. The esterification reaction of FFA in CSO with methanol over SnCl<sub>2</sub>·2H<sub>2</sub>O is illustrated in Figure 1.

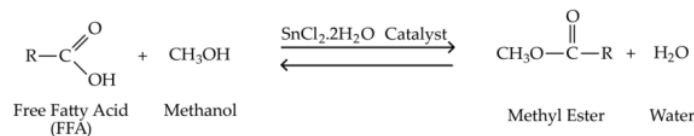**Figure 1.** Esterification of FFA with Methanol in the Presence of SnCl<sub>2</sub>·2H<sub>2</sub>O Catalyst.


Based on the stoichiometry, one mole FFA requires one mole methanol to precede the esterification reaction [41]. However, the Fischer esterification reaction is an equilibrium limited reaction. Thus, a great excess of methanol reactant should be introduced to shift the equilibrium towards the product formation [42]. In this work, a fixed CSO to methanol ratio of 1:30 was applied for all the experiments. To intensify the mixing between the reactants and catalyst, the agitation speed was kept at 1000 rpm. The rapid agitation is beneficial to reduce the film thickness between the reactants and promote the mass transfer [42]. The experimental results are demonstrated in Figures 2 and 3.

Figure 2 presents the effect of the catalyst molar ratio on the reaction conversion for the reaction conducted at a fixed reaction temperature, molar ratio of CSO and methanol, and reaction time of 60 °C, 1:30, and 120 min, respectively. The effect of the catalyst concentration was studied at the range of 1–7% w/w CSO. Catalyst offers an altered reaction route with lower activation energy. Hence, it causes a higher percentage of collisions between the reactants' molecules when they reach the minimum energy to react. It can be observed that the reaction conversion was enhanced to 73.75% with an increase in catalyst concentration from 1% to 5%. The higher reaction conversion was accomplished on account of the increased number of active sites available for the reaction [43,44]. Thus, it accelerated the reaction to reach the equilibrium. However, it was revealed that the employment of 7% catalyst did not further raise the reaction conversion. Instead, the conversion tended to slightly decline to 65.85%. This means that the excessive addition of catalyst will not

provide a comparative influence on the conversion improvement when the contact process has already arrived at the maximum [45].

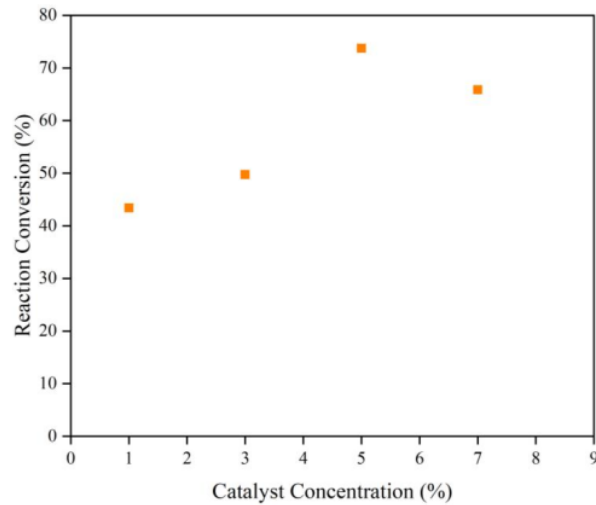

**Figure 2.** Effect of the Catalyst Concentration on the Reaction Conversion of FFA Esterification in CSO over  $\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$  Catalyst at the Reaction Temperature of  $60^\circ\text{C}$ , Molar Ratio of CSO and methanol of 1:30, and Reaction Time of 120 min.

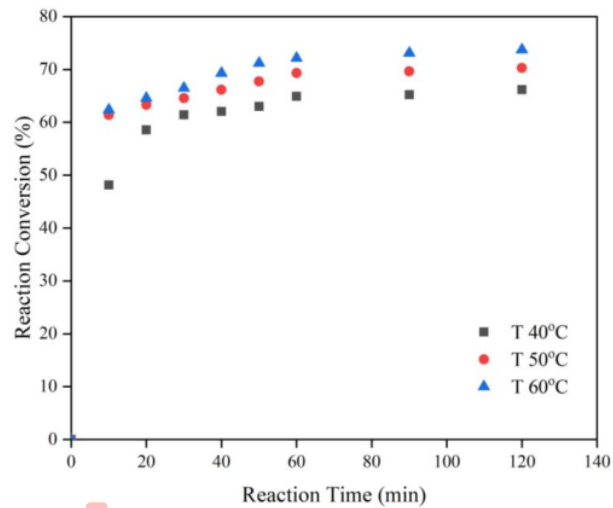

**Figure 3.** Effect of the Temperature and Reaction Time on the Reaction Conversion of FFA Esterification in CSO over  $\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$  Catalyst at the Molar Ratio of CSO: methanol of 1:30 and Catalyst Concentration of 5%.

Figure 3 exhibits the effects of the temperature and the reaction time on the reaction conversion for the reaction carried out at a fixed catalyst concentration of 5% and molar ratio of CSO: methanol of 1:30. The reaction temperature was examined at 40, 50 and  $60^\circ\text{C}$  and the reaction time was inspected at 0–120 min. It was disclosed that the rising of the temperature brought about the extensively higher reaction conversion. Esterification is an endothermic reaction; therefore the reaction rate increased with the temperature [46]. A

rise in the temperature will also improve the translation and the rotation of the reactants' molecules and lower the liquid viscosity, which will enhance the diffusion rate of the reactants to the active sites of the catalyst [45]. The effective mass transfer has a beneficial impact on the higher total reaction rate and higher reaction conversion. The highest conversion of 73.75% was obtained at 60 °C, which was near to the boiling point of the methanol. A further increase in the temperature at a similar atmospheric pressure will not promote the conversion since it will exceed the boiling point, and hence part of the methanol in the liquid phase will change to the gas phase. The result was in a good agreement with Handayani et al. [47]. The longer the reaction time, the higher the conversion that was attained. However, a sharp acceleration was shown in the first 10 min of the reaction. It was attributed to the high concentration of the reactant at the beginning of the reaction. To determine the optimum process condition which led to the best reaction conversion, analysis using Box–Behnken Design (BBD) in Response Surface Methodology (RSM) was also carried out.

### 3.2. Model Fitting in Box–Behnken Design (BBD)

Response Surface Methodology (RSM) using Box–Behnken Design (BBD) is broadly applied to determine the optimum condition of the variables which results in the desired response. It is also practical for evaluating the effects of the independent variables and the interaction between the independent variables [48]. In this work, BBD was employed to examine the effects and interactions of the independent variables (reaction time, reaction temperature, and catalyst concentration) to determine the optimum condition which produced the highest ester yield and the lowest FFA content in the esterification of CSO using methanol over SnCl<sub>2</sub>·2H<sub>2</sub>O catalyst.

The Box–Behnken response surface design and corresponding response values in this work, including the comparison between the experimental data and the prediction value as well as the errors, are revealed in Table 3. Error is the disparity between the observed and the predictive values, and, accordingly, it can be used to evaluate the accuracy of the model. The error values in this study were calculated in term of mean absolute percentage error (MAPE) as conveyed in Equation (3). It was revealed that the MAPE of the FFA conversion and the FFA content responses were 2.2704% and 3.3410%. The values of MAPE were far less than 10%, indicating the high correctness of the prediction. Generally, values of MAPE below 10% designate a high accuracy of prediction, whereas the values of 10–20%, 20–50%, and higher than 50% imply good, fair, and inaccurate forecasting, respectively [49].

Table 3. The Box–Behnken Response Surface Design and Corresponding Response Values.

Run	Temperature	Reaction Time (min)	Catalyst Concentration (%) C	FFA Conversion %		Error (MAPE) %	FFA Content (%)		Error (MAPE) %
	(°C) A			Experiment	Prediction		Experiment	Prediction	
1	40	120	5	66.161	65.963	0.2987	6.227	6.264	0.5862
2	40	60	5	64.896	64.619	0.4267	6.460	6.511	0.7895
3	60	90	3	46.237	44.695	3.3348	9.894	10.178	2.8704
4	40	90	7	52.878	54.420	2.9160	8.672	8.388	3.2749
5	60	90	7	65.528	66.595	1.6289	6.344	6.148	3.0974
6	50	120	3	44.023	45.288	2.8735	10.301	10.068	2.2619
7	60	120	5	73.751	74.028	0.3755	4.831	4.780	1.0557
8	50	60	7	62.682	61.417	2.0181	6.867	7.100	3.3930
9	50	90	5	63.631	65.634	2.0181	6.693	6.324	5.5132
10	40	90	3	42.125	41.058	2.5339	10.650	10.847	1.8451
11	60	60	5	72.170	72.368	0.2738	5.122	5.086	0.7126
12	50	60	3	41.809	43.153	3.2153	10.709	10.462	2.3111
13	50	90	5	69.640	65.634	5.7524	5.587	6.324	13.1967
14	50	120	7	63.631	62.287	2.1125	6.693	6.941	3.6979
15	50	90	5	63.631	65.634	3.1478	6.693	6.324	5.5087
MAPE (%)						2.2704			3.3410

There are various models that are available for the optimization using RSM. In this work, four polynomial models (viz., linear, 2FI or two-factor interaction, quadratic, and cubic) were assessed to decide the most appropriate model to suit the experimental data. The above mentioned models have been extensively studied in the field of bioresources



processing research [25,50]. The evaluation of the models was carried out using two different statistical testing methods, i.e., the sequential model (sum of squares) and the model summary tests. Based on the sequential model sum of squares test (Table 4) and the model summary test (Table 5), it was found that the suggested model to optimize the FFA conversion and the FFA content in the case of CSO esterification over SnCl<sub>2</sub>·2H<sub>2</sub>O catalyst was the quadratic model. The quadratic model was designated due to the facts that it provided the lowest p value as indicated in Table 4, and, at the same time, it shown the highest adjusted R<sup>2</sup> and predicted R<sup>2</sup> as demonstrated in Table 5.

Table 4. Sequential Model (Sum of Squares) Test.

Component	Sum of Square	Degree of Freedom	Mean Square	F-Value	p-Value	Remarks
Sequential (Sum of Square) for the FFA Conversion						
Mean	53,138.62	1	53,138.62			
Linear	751.26	3	250.42	2.87	0.09	
2FI	18.65	3	6.22	0.05	0.98	
Quadratic	903.67	3	301.22	39.48	0.0007	Suggested
Cubic	14.08	3	4.69	0.39	0.7758	Aliased
Residual	24.07	2	12.04			
Total	54,850.36	15	3656.69			
Sequential (Sum of Square) for the FFA Content						
Mean	832.43	1	832.43			
Linear	25.44	3	8.48	2.87	0.09	
2FI	0.63	3	0.21	0.05	0.98	
Quadratic	30.60	3	10.20	39.44	0.0007	Suggested
Cubic	0.48	3	0.16	0.39	0.7756	Aliased
Residual	0.82	2	0.41			
Total	890.40	15	59.36			

Table 5. Model Summary Test.

Component	Standard Deviation	R <sup>2</sup>	Adjusted R <sup>2</sup>	Predicted R <sup>2</sup>	Press	Remarks
Model Summary for the FFA Conversion						
Linear	9.34	0.44	0.29	−0.12	1921.57	
2FI	10.85	0.45	0.04	−1.59	4446.52	
Quadratic	2.76	0.98	0.94	0.84	279.43	Suggested
Cubic	3.47	0.99	0.90		*	Aliased
Model Summary for the FFA Content						
Linear	1.72	0.44	0.29	−0.12	65.07	
2FI	2.00	0.45	0.04	−1.59	150.57	
Quadratic	0.51	0.98	0.94	0.84	9.47	Suggested
Cubic	0.64	0.99	0.90		*	Aliased

\* means not defined.

The empirical correlation of the variables and the response based on the quadratic model resulting from the BBD can be stated in the form of a second order polynomial equation. The general equation for the second order polynomial regression model is written in Equation (4).

$$Y = \beta_0 + \sum_{i=1}^k (\beta_i X_i) + \sum_{i=1}^k (\beta_{ii} X_i^2) + \sum_{ii=1}^k \sum_{j>1}^k (\beta_{ij} X_i X_j) \tag{4}$$

Y indicates the predicted response,  $\beta_0$  is a constant,  $\beta_i$  is a coefficient for the linear,  $\beta_{ii}$  is the coefficient for the quadratic, and  $\beta_{ij}$  is the interactive coefficient [29,51].

Thus, the definitive equations for the FFA conversion and FFA content are revealed in Equations (5) and (6), respectively.

$$\begin{aligned} \text{FFA Conversion (\%)} = & 3.47466 - 1.29512 A - 0.457250 B + 37.23375 C + \\ & 0.000263 AB + 0.106725 AC - 0.005271 BC + \\ & 0.011331 A^2 + 0.002753 B^2 - 3.76878 C^2 \end{aligned} \quad (5)$$

$$\begin{aligned} \text{FFA Content (\%)} = & 17.746 - 0.238292 A - 0.4084117 B + 6.85158 C + \\ & 0.000048 AB + 0.19650 AC - 0.000975 BC + 0.002084 A^2 + \\ & 0.000507 B^2 - 0.693521 C^2 \end{aligned} \quad (6)$$

where *A*, *B*, and *C* are the temperature (°C), reaction time (min), and catalyst concentration (%), respectively.

### 3.3. Statistical Analysis Using ANOVA

The quadratic model as the most appropriate model was thenceforth analyzed using analysis of variance (ANOVA). The significance of the actual data to the different models based on their associated *p*-values is displayed in Tables 6 and 7. Table 6 shows the statistical analysis using ANOVA to predict the FFA conversion in the esterification of CSO. The significance of each constant and the intensity of interaction were proved by the *p*-value. Influences lower than 0.05 are significant [50]. It can be observed that the *F* value was 24.37 at the *p*-value < 0.05, denoting that the model was significant. In this investigation, it was discovered that the affecting variables were two linear coefficients (*A* and *C*) and one quadratic coefficient (*C*<sup>2</sup>). This implies that the temperature (*A*) and catalyst concentration (*C*) were significant to the model, but the reaction time (*B*) was insignificant. The adeq precision value is the measurement of the ratio of the signal against the interference, in which the expected ratio is >4. Table 6 demonstrates that the adeq precision was 14.6107, revealing that the model was significant [52]. The lack of fit was 14.08 at a *p*-value of 0.78, which was determined to be significant. It can be suggested that the model is suitable for the prediction of the FFA conversion.

**Table 6.** Analysis of the Variance and Regression Coefficients of the BBD Quadratic Model to Predict the FFA Conversion.

Source	Sum of Square	DF	Mean Square	F Value	<i>p</i> -Value	
Model	1673.58	9	185.95	24.37	0.00	Significant
A Temperature (°C)	125.03	1	125.03	16.39	0.01	
B Reaction Time (min)	4.51	1	4.51	0.59	0.48	
C Catalyst Concentration (%)	621.72	1	621.72	81.48	0.00	
AB	0.03	1	0.03	0.003	0.96	
AC	18.22	1	18.22	2.39	0.18	
BC	0.40	1	0.40	0.05	0.83	
A <sup>2</sup>	4.74	1	4.74	0.62	0.47	
B <sup>2</sup>	22.66	1	22.66	2.97	0.15	
C <sup>2</sup>	839.11	1	839.11	109.97	0.00	
Residual	38.15	5	7.63			Not Significant
Lack of Fit	14.08	3	14.08	0.39	0.78	
Pure Error	24.08	2	12.04			
Cor Total	1711.73	14				
Adeq Precision	14.62					
R <sup>2</sup>	0.98					

**Table 7.** Analysis of the Variance and Regression Coefficients of the BBD Quadratic Model to Predict the FFA Content.


Source	Sum of Square	DF	Mean Square	F Value	p-Value	
Model	56.67	9	6.30	24.35	0.00	Significant
X <sub>1</sub>	4.23	1	4.23	16.36	0.01	
X <sub>2</sub>	0.15	1	0.15	0.59	0.48	
X <sub>3</sub>	21.05	1	21.05	81.41	0.00	
X <sub>12</sub>	0.00	1	0.00	0.00	0.96	
X <sub>13</sub>	0.62	1	0.62	2.39	0.18	
X <sub>23</sub>	0.01	1	0.01	0.05	0.83	
X <sub>1</sub> <sup>2</sup>	0.16	1	0.16	0.62	0.47	
X <sub>2</sub> <sup>2</sup>	0.77	1	0.77	2.97	0.15	
X <sub>3</sub> <sup>2</sup>	28.41	1	28.41	109.88	0.00	
Residual	1.29	5	0.26			
Lack of Fit	0.48	3	0.16	0.39	0.78	Not Significant
Pure Error	0.82	2	0.41			
Cor Total	57.96	14				
R <sup>2</sup>	0.98					
Adeq Precision	14.61					

The use of the ANOVA regression model to predict the left over FFA content after the esterification reaction of CSO can be observed in Table 7. The experimental data were analyzed using ANOVA, and the significant regression coefficient was determined based on the *p*-value, in which a *p*-value < 0.05 denotes that the model is significant. The value of adeq precision is the magnitude of the ratio of the signal to the disturbance, wherein the desirable value is >4 [52,53]. This model showed the adeq precision of 14.6107, indicating that the model is accurate.


#### 3.4. Optimization of the Process Variables Using BBD

The optimization of the process variables to obtain the targeted response variables was performed using a quadratic model of BBD. Primarily, the influences of the process variables, such as temperature, reaction time, and catalyst concentration, to the response variables, viz., the reaction conversion and the FFA content in the CSO esterification over SnCl<sub>2</sub>·2H<sub>2</sub>O catalyst, were investigated using BBD in RSM. Based on the model selected, analysis of the main effect and the interaction of the process variables to the response variable using 3D RSM was carried out. The resulting 3D graphs were developed from maintaining one constant variable (derived from the midpoint) and varying two other variables. Therefore, the effect of each process variable on the response variable can be identified.

Figures 4 and 5 disclose that the reaction conversion increased and the FFA content decreased with the temperature up to 60 °C, respectively. The intensification of the catalyst concentration from 3% to 5% enhanced the reaction conversion and diminished the FFA content considerably. This was due to the increased number of reactant molecules which were activated by the carbonyl polarization due to the higher amount of Sn<sup>+2</sup> catalyst. Hence, the nucleophilic attack by methanol could occur more frequently and effectively, leading to the higher reaction conversion. Oppositely, the leftover FFA content was reduced [54]. There are various proposed mechanisms concerning the carbonyl group activation by tin catalyst, yet the carbonyl polarization will be auspicious when attacked by the hydroxyl group [55]. However, the further increase of the catalyst from 5% to 7% did not provide a meaningful effect in terms of improving the reaction conversion and lessening the FFA content. As a matter of fact, it can be observed that the employment of 7% catalyst increased the FFA content. Marso et al. [56] described how an excessive utilization of the catalyst beyond the optimum concentration could form an emulsion which increased the viscosity and thus hindered the contact between the CSO and the methanol. Consequently, it lowered the reaction conversion. Hence, the residual FFA in the oil was higher.

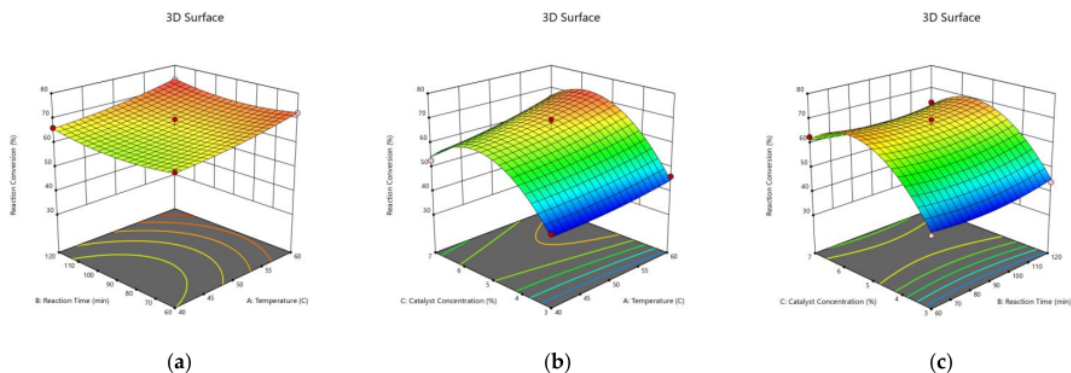


**Figure 4.** Three Dimensional (3D) Response Surface of the Effects of the Process Variables on the Reaction Conversion. (a) Catalyst Concentration of 5%; (b) Reaction Time of 90 min; (c) Reaction Temperature of 50 °C.

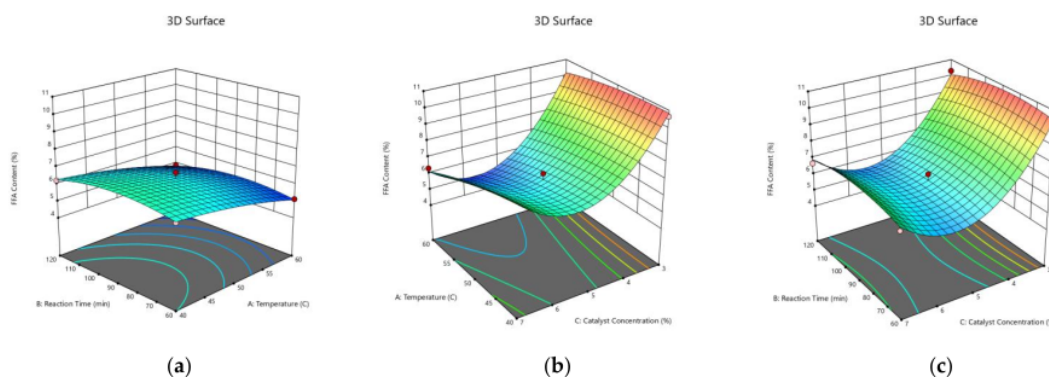

**Figure 5.** Three Dimensional (3D) Response Surface of the Effects of Process Variables on the FFA Content in after the Undergoing the Esterification Reaction. (a) Catalyst Concentration of 5%; (b) Reaction Time of 90 min; (c) Reaction Temperature of 50 °C.

In this study, the Derringer method was utilized to optimize the reaction conversion and the reduction of FFA content via CSO esterification over  $\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$  catalyst. The Derringer method is a popular desirability function-based approach to solving a problem comprising a simultaneous optimization of several response variables. Derringer and Suich [57] modified the previous Harrington's procedure by converting the response into a desirability function [58]. The values of desirability functions are between 0 and 1. Mathematically, the general approach is to convert each response into an individual desirability function (d) that varies over the range  $0 \leq d \leq 1$  [59]. The value of 0 implies that the factors present unfavorable response. On the other hand, the value of 1 relates to the optimal condition of the examined factors and indicates that the responses are at their targets. This approach simplifies the multivariate optimization. Due to its simplicity and flexibility, the Derringer desirability function has been broadly applied in multiple responses optimization to find out the independent variables condition which brings about the optimal values of the response variables [60]. Based on the optimization process, Figure 6 reveals that the optimum reaction conversion and FFA content were 75.03% and 4.59%, respectively, which were achieved at the following operation condition: a reaction temperature of 59.36 °C, a reaction time of 117.8 min, and a catalyst concentration of 5.61%. The value of desirability obtained was 1, indicating the optimal condition of the studied parameters. This result

was slightly lower than that for the similar reaction which was conducted using sulfuric acid catalyst at the reaction temperature, catalyst loading, and reaction time of 59.09 °C, 1.98% g/g CSO, and 119.95 min, respectively, resulting in the reaction conversion of 78.27% and the FFA content of 4% [25]. Despite this slight lower conversion, the application of heterogeneous  $\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$  catalyst is greatly preferable to the sulfuric acid catalyst since it is more environmentally friendly, reusable, less corrosive, and easier in handling and separation. The result of this work offers a green alternative of synthesizing renewable bio based fatty ester from CSO as precursor of epoxy ester plasticizer.

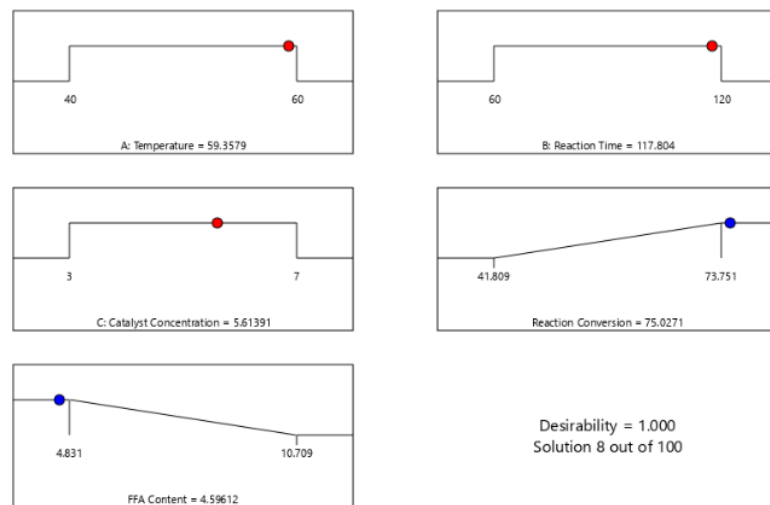

**Figure 6.** Optimization of Reaction Conversion and FFA Content using BBD Quadratic Model in RSM.

#### 4. Conclusions

The esterification of FFA in *Calophyllum inophyllum* Seed Oil (CSO) using methanol in the presence of  $\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$  catalyst has been conducted as an alternative way to produce fatty acid ester as a green precursor of epoxy ester plasticizer. In this investigation, the interactive and individual effects from three experimental variables (temperature, reaction time, and catalyst free concentration) on reaction conversion and residual free fatty acid (FFA) content were studied by employing the Box–Behnken Design (BBD) of Response Surface Methodology (RSM) technique. The quadratic model in BBD was selected for the optimization of the reaction conversion and the decreasing of the FFA content. The BBD analysis showed that the optimum FFA conversion and residual FFA content were 75.03% and 4.59%, respectively, attained at the following process condition: a reaction temperature of 59.36 °C, a reaction time of 117.80 min, and a catalyst concentration of 5.61%. The fatty acid ester generated is subsequently ready for the further epoxidation process to produce epoxy plasticizer in polymeric material production.

**Author Contributions:** Conceptualization, R.D.K.; methodology, R.D.K. and H.P.; software, H.P.; validation, R.D.K. and H.P.; formal analysis, N.D.A. and E.D.N.A.; investigation, R.D.K.; resources, R.D.K.; data curation, R.D.K. and D.H.; writing—original draft preparation, R.D.K., N.D.A. and E.D.N.A.; writing—review and editing, R.D.K., H.P. and D.H.; visualization, N.D.A. and E.D.N.A.; supervision, R.D.K. and H.P.; project administration, R.D.K.; funding acquisition, R.D.K. All authors have read and agreed to the published version of the manuscript.

**Funding:** Financial support from the Research and Community Service Institute (LPPM) of Universitas Negeri Semarang through the DIPA UNNES research grant with the contract number of 101.23.4/UN37/PPK.3.1/2020 is highly acknowledged.



**Data Availability Statement:** Not applicable.

**Acknowledgments:** The authors would like to thank to the Research and Community Service Institute (LPPM) of Universitas Negeri Semarang through the DIPA UNNES research grant with the contract number of 101.23.4/UN37/PPK.3.1/2020 for the funding.

**Conflicts of Interest:** The authors declare no conflict of interest.

## References

1. Vieira, M.G.A.; Da Silva, M.A.; Dos Santos, L.O.; Beppu, M.M. Natural-Based Plasticizers and Biopolymer Films: A Review. *Eur. Polym. J.* **2011**, *47*, 254–263. [[CrossRef](#)]
2. Junthip, J.; Chaipalee, N.; Sangsorn, Y.; Maspornpat, C.; Jitcharoen, J.; Limrungruengrat, S.; Chotchuangchutchaval, T.; Martwong, E.; Sukhawipat, N. The Use of New Waste-Based Plasticizer Made from Modified Used Palm Oil for Non-Glutinous Thermoplastic Starch Foam. *Polymers* **2022**, *14*, 3997. [[CrossRef](#)] [[PubMed](#)]
3. Janik, W.; Ledniowska, K.; Nowotarski, M.; Kudla, S.; Knapczyk-Korczak, J.; Stachewicz, U.; Nowakowska-Bogdan, E.; Sabura, E.; Nosal-Kovalenko, H.; Turczyn, R.; et al. Chitosan-Based Films with Alternative Eco-Friendly Plasticizers: Preparation, Physicochemical Properties and Stability. *Carbohydr. Polym.* **2023**, *301*, 120277. [[CrossRef](#)]
4. Edwards, L.; McCray, N.L.; VanNoy, B.N.; Yau, A.; Geller, R.J.; Adamkiewicz, G.; Zota, A.R. Phthalate and Novel Plasticizer Concentrations in Food Items from U.S. Fast Food Chains: A Preliminary Analysis. *J. Expo. Sci. Environ. Epidemiol.* **2022**, *32*, 366–373. [[CrossRef](#)]
5. Kim, D.Y.; Chun, S.H.; Jung, Y.; Mohamed, D.F.M.S.; Kim, H.S.; Kang, D.Y.; An, J.W.; Park, S.Y.; Kwon, H.W.; Kwon, J.H. Phthalate Plasticizers in Children's Products and Estimation of Exposure: Importance of Migration Rate. *Int. J. Environ. Res. Public Health* **2020**, *17*, 8582. [[CrossRef](#)] [[PubMed](#)]
6. Jia, P.; Xia, H.; Tang, K.; Zhou, Y. Plasticizers Derived from Biomass Resources: A Short Review. *Polymers* **2018**, *10*, 1303. [[CrossRef](#)]
7. Hosney, H.; Nadiem, B.; Ashour, I.; Mustafa, I.; El-Shibiny, A. Epoxidized Vegetable Oil and Bio-Based Materials as PVC Plasticizer. *J. Appl. Polym. Sci.* **2018**, *135*, 46270. [[CrossRef](#)]
8. Bai, Y.; Wang, J.; Liu, D.; Zhao, X. Conversion of Fatty Acid Methyl Ester to Epoxy Plasticizer by Auto-Catalyzed in Situ Formation of Performic Acid: Kinetic Modeling and Application of the Model. *J. Clean. Prod.* **2020**, *259*, 120791. [[CrossRef](#)]
9. Pan, S.; Hou, D.; Yang, G.; Xie, Q.; Yan, S.; Zeng, Q.; Wang, Z.; Chen, Y.; Fan, H. Epoxidized Methyl Ricinoleate Bio-Plasticizer with a Pendant Acetate Ester for PVC Artificial Material: Circumventing Existing Limit on Achievable Migration Resistance. *J. Leather Sci. Eng.* **2019**, *1*, 2. [[CrossRef](#)]
10. Galli, F.; Nucci, S.; Pirola, C.; Bianchi, C.L. Epoxy Methyl Soyate as Bio-Plasticizer: Two Different Preparation Strategies. *Chem. Eng. Trans.* **2014**, *37*, 601–606. [[CrossRef](#)]
11. Ergashev, I.M.; Mamirzayev, M.A.; Sedalova, I.S.; Suyunov, S. Study of Triglycerides in Vegetable Oils by Gas Chromatography. *Asian J. Phys. Chem. Math.* **2022**, *5*, 93–96.
12. Schuchardt, U.; Sercheli, R.; Matheus, R. Transesterification of Vegetable Oils: A Review. *J. Braz. Chem. Soc.* **1998**, *9*, 199–210. [[CrossRef](#)]
13. Simpen, I.; Winaya, I.S.; Subagia, I.G.A.; Suyasa, I.B. Solid Catalyst in Esterification and Transesterification Reactions for Biodiesel Production: A Review. *Int. J. Eng. Emerg. Technol.* **2020**, *5*, 168–174.
14. Di Pietro, M.E.; Mannu, A.; Mele, A. NMR Determination of Free Fatty Acids in Vegetable Oils. *Processes* **2020**, *8*, 410. [[CrossRef](#)]
15. Edyson, E.; Murgianto, F.; Ardiyanto, A.; Astuti, E.J.; Ahmad, M.P. Preprocessing Factors Affected Free Fatty Acid Content in Crude Palm Oil Quality. *J. Ilmu Pertan. Indones.* **2022**, *27*, 177–181. [[CrossRef](#)]
16. Kusumaningtyas, R.D.; Ratrianti, N.; Purnamasari, I.; Budiman, A. Kinetics Study of Jatropha Oil Esterification with Ethanol in the Presence of Tin (II) Chloride Catalyst for Biodiesel Production. *AIP Conf. Proc.* **2017**, *1788*, 030086. [[CrossRef](#)]
17. Hidalgo, P.; Álvarez, S.; Hunter, R.; Sánchez, A. Epoxidation of Fatty Acid Methyl Esters Derived from Algae Biomass to Develop Sustainable Bio-Based Epoxy Resins. *Polymers* **2020**, *12*, 2313. [[CrossRef](#)]
18. Sustaita-Rodríguez, A.; Ramos-Sánchez, V.H.; Camacho-Dávila, A.A.; Zaragoza-Galán, G.; Espinoza-Hicks, J.C.; Chávez-Flores, D. Lipase Catalyzed Epoxidation of Fatty Acid Methyl Esters Derived from Unsaturated Vegetable Oils in Absence of Carboxylic Acid. *Chem. Cent. J.* **2018**, *12*, 39. [[CrossRef](#)]
19. Meng, Y.; Taddeo, F.; Aguilera, A.F.; Cai, X.; Russo, V.; Tolvanen, P.; Leveneur, S. The Lord of the Chemical Rings: Catalytic Synthesis of Important Industrial Epoxide Compounds. *Catalysts* **2021**, *11*, 765. [[CrossRef](#)]
20. Benaniba, M.T.; Benaniba, M.T.; Belhaneche-Bensemra, N.; Gelbard, G. Epoxidation of Sunflower Oil with Peroxoacetic Acid in Presence of Ion Exchange Resin by Various Processes Polymer Recycling View Project Miscible Polymer Blends View Project Epoxidation of Sunflower Oil with Peroxoacetic Acid in Presence of Ion Exchange. *Energy Educ. Sci. Technol.* **2008**, *21*, 71–82.
21. Ifa, L.; Syarif, T.; Sabara, Z.; Nurjannah, N.; Munira, M.; Aryani, F. Study on the Kinetics of Epoxidation Reaction of RBD Palm Olein. *IOP Conf. Ser. Earth Environ. Sci.* **2018**, *175*, 012035. [[CrossRef](#)]
22. Musik, M.; Janus, E.; Pelech, R.; Salaciński, L. Effective Epoxidation of Fatty Acid Methyl Esters with Hydrogen Peroxide by the Catalytic System H3pw12o40/ Quaternary Phosphonium Salts. *Catalysts* **2021**, *11*, 1058. [[CrossRef](#)]

23. Ginigini, J.; Lecellier, G.J.; Nicolas, M.; Nour, M.; Hnawia, E.; Lebouvier, N.; Herbette, G.; Lockhart, P.; Raharivelomanana, P. Chemodiversity of *Calophyllum inophyllum* L. Oil Bioactive Components Related to Their Specific Geographical Distribution in the South Pacific Region. *PeerJ* **2019**, *2019*, 6896. [[CrossRef](#)] [[PubMed](#)]
24. Akram, F.; Haq, I.U.; Raja, S.I.; Mir, A.S.; Qureshi, S.S.; Aqeel, A.; Shah, F.I. Current Trends in Biodiesel Production Technologies and Future Progressions: A Possible Displacement of the Petro-Diesel. *J. Clean. Prod.* **2022**, *370*, 133479. [[CrossRef](#)]
25. Kusumaningtyas, R.D.; Prasatiawan, H.; Putri, R.D.A.; Triwibowo, B.; Kurnita, S.C.F.; Anggraeni, N.D.; Veny, H.; Hamzah, F.; Rodhi, M.N.M. Optimisation of Free Fatty Acid Removal in Nyamplung Seed Oil (*Calophyllum inophyllum* L.) Using Response Surface Methodology Analysis. *Pertanika J. Sci. Technol.* **2021**, *29*, 2605–2623. [[CrossRef](#)]
26. Ferreira, A.B.; Lemos Cardoso, A.; da Silva, M.J. Tin-Catalyzed Esterification and Transesterification Reactions: A Review. *ISRN Renew. Energy* **2012**, *2012*, 142857. [[CrossRef](#)]
27. Da Silva, M.J.; Cardoso, A.L. Assessing the Activity of Solid-Suported SnCl<sub>2</sub> Catalysts on the Oleic Acid Esterification for Biodiesel Production. *J. Thermodyn. Catal.* **2016**, *7*, 1000173. [[CrossRef](#)]
28. Sert, E.; Atalay, F.S. Application of Green Catalysts for the Esterification of Benzoic Acid with Different Alcohols. *Celal Bayar Üniversitesi Fen Bilim. Derg.* **2017**, *13*, 907–912. [[CrossRef](#)]
29. Polat, S.; Sayan, P. Application of Response Surface Methodology with a Box–Behnken Design for Struvite Precipitation. *Adv. Powder Technol.* **2019**, *30*, 2396–2407. [[CrossRef](#)]
30. Czyrski, A.; Jarzebski, H. Response Surface Methodology as a Useful Tool for Evaluation of the Recovery of the Fluoroquinolones from Plasma-the Study on Applicability of Box–Behnken Design, Central Composite Design and Doehlert Design. *Processes* **2020**, *8*, 473. [[CrossRef](#)]
31. Riswanto, F.D.O.; Rohman, A.; Pramono, S.; Martono, S. Application of Response Surface Methodology as Mathematical and Statistical Tools in Natural Product Research. *J. Appl. Pharm. Sci.* **2019**, *9*, 125–133. [[CrossRef](#)]
32. Sharma, Y.C.; Yadav, M.; Upadhyay, S.N. Latest Advances in Degumming Feedstock Oils for Large-Scale Biodiesel Production. *Biofuels Bioprod. Biorefining* **2019**, *13*, 174–191. [[CrossRef](#)]
33. Camacho, J.N.; Romero, R.; Galván Muciño, G.E.; Martínez-Vargas, S.L.; Pérez-Alonso, C.; Natividad, R. Kinetic Modeling of Canola Oil Transesterification Catalyzed by Quicklime. *J. Appl. Res. Technol.* **2018**, *16*, 446–454. [[CrossRef](#)]
34. Yu, H.; Niu, S.; Lu, C.; Wei, W.; Zhang, X. Biodiesel Synthesis by Transesterification Using Coal-Based Solid Acid Catalyst. *IOP Conf. Ser. Earth Environ. Sci.* **2021**, *634*, 012041. [[CrossRef](#)]
35. Ho, W.W.S.; Ng, H.K.; Gan, S. Biodiesel Synthesis from Refined Palm Oil Using a Calcium Oxide Impregnated Ash-Based Catalyst: Parametric, Kinetics, and Product Characterization Studies. *Catalysts* **2022**, *12*, 706. [[CrossRef](#)]
36. Banchero, M.; Gozzelino, G. A Simple Pseudo-Homogeneous Reversible Kinetic Model for the Esterification of Different Fatty Acids with Methanol in the Presence of Amberlyst-15. *Energies* **2018**, *11*, 1843. [[CrossRef](#)]
37. Intarat, N.; Somnuk, K.; Theppaya, T.; Prateepchaikul, G. Acid Value Reduction Process in Mixed Crude Palm Oil by Using Low-Grade Ethanol. *Adv. Mater. Res.* **2014**, *1025–1026*, 677–682. [[CrossRef](#)]
38. Kurniati, S.; Soeparman, S.; Yuwono, S.S.; Hakim, L. Characteristics and Potential of Nyamplung (*Calophyllum inophyllum* L.) Seed Oil from Kebumen, Central Java, as a Biodiesel Feedstock. *Int. Res. J. Adv. Eng. Sci.* **2018**, *3*, 148–152.
39. Kusumaningtyas, R.D.; Prasatiawan, H.; Pratama, B.R.; Prasetya, D.; Hisyam, A. Esterification of Non-Edible Oil Mixture in Reactive Distillation Column over Solid Acid Catalyst: Experimental and Simulation Study. *J. Phys. Sci.* **2018**, *29*, 212–226. [[CrossRef](#)]
40. Mohan, S.K.; Viruthagiri, T.; Arunkumar, C. Statistical Optimization of Process Parameters for the Production of Tannase by *Aspergillus Flavus* under Submerged Fermentation. *3 Biotech* **2014**, *4*, 159–166. [[CrossRef](#)]
41. Ding, J.; Xia, Z.; Lu, J. Esterification and Decidification of a Waste Cooking Oil (TAN 68.81 Mg KOH/g) for Biodiesel Production. *Energies* **2012**, *5*, 2683–2691. [[CrossRef](#)]
42. Khan, Z.; Javed, F.; Shamair, Z.; Hafeez, A.; Fazal, T.; Aslam, A.; Zimmerman, W.B.; Rehman, F. Current Developments in Esterification Reaction: A Review on Process and Parameters. *J. Ind. Eng. Chem.* **2021**, *103*, 80–101. [[CrossRef](#)]
43. Ngadi, N.; Ma, L.N.; Alias, H.; Johari, A.; Rahman, R.A.; Mohamad, M. Production of Biodiesel from Waste Cooking Oil via Ultrasonic-Assisted Catalytic System. *Appl. Mech. Mater.* **2014**, *699*, 552–557. [[CrossRef](#)]
44. Khudsange, C.R.; Wasewar, K.L. Process Intensification of Esterification Reaction for the Production of Propyl Butyrate by Pervaporation. *Resour. Technol.* **2017**, *3*, 88–93. [[CrossRef](#)]
45. Nindya, C.C.S.; Anggara, D.R.; Nuryoto; Teguh, K. Esterification Glycerol (by Product in Biodiesel Production) with Oleic Acid Using Mordenite Natural Zeolite as Catalyst: Study of Reaction Temperature and Catalyst Loading Effect. *IOP Conf. Ser. Mater. Sci. Eng.* **2020**, *909*, 012001. [[CrossRef](#)]
46. Rani, K.N.P.; Neeharika, T.S.V.R.; Vardhan, G.H.; Kumar, T.P.; Devi, B.L.A.P. The Kinetics of the Esterification of Free Fatty Acids in *Jatropha* Oil Using Glycerol Based Solid Acid Catalyst. *Eur. J. Sustain. Dev. Res.* **2020**, *4*, em0116. [[CrossRef](#)]
47. Handayani, P.A.; Wulansarie, R.; Husaen, P.; Ulfayanti, I.M. Esterification of Nyamplung (*Calophyllum inophyllum*) Oil With Ionic Liquid Catalyst of BmimhsO<sub>4</sub> and Microwaves-Assisted. *J. Bahan Alam Terbarukan* **2018**, *7*, 59–63. [[CrossRef](#)]
48. Ahmadian-Kouchaksaraie, Z.; Niazmand, R. Supercritical Carbon Dioxide Extraction of Antioxidants from Crocus Sativus Petals of Saffron Industry Residues: Optimization Using Response Surface Methodology. *J. Supercrit. Fluids* **2017**, *121*, 19–31. [[CrossRef](#)]
49. Montaña Moreno, J.J.; Palmer Pol, A.; Sesé Abad, A.; Cajal Blasco, B. Using the R-MAPE Index as a Resistant Measure of Forecast Accuracy. *Psicothema* **2013**, *25*, 500–506. [[CrossRef](#)]

50. Ahmad, A.; Rehman, M.U.; Wali, A.F.; El-Serehy, H.A.; Al-Misned, F.A.; Maodaa, S.N.; Aljawdah, H.M.; Mir, T.M.; Ahmad, P. Box–Behnken Response Surface Design of Polysaccharide Extraction from *Rhododendron Arboreum* and the Evaluation of Its Antioxidant Potential. *Molecules* **2020**, *25*, 3835. [[CrossRef](#)]
51. Jyoti, G.; Keshav, A.; Anandkumar, J. Optimization of Esterification of Acrylic Acid and Ethanol by Box–Behnken Design of Response Surface Methodology. *Indian J. Chem. Technol.* **2019**, *26*, 89–94.
52. Mia, M. Mathematical Modeling and Optimization of MQL Assisted End Milling Characteristics Based on RSM and Taguchi Method. *Meas. J. Int. Meas. Confed.* **2018**, *121*, 249–260. [[CrossRef](#)]
53. Variyana, Y.; Muchammad, R.S.C.; Mahfud, M. Box–Behnken Design for the Optimization Using Solvent-Free Microwave Gravity Extraction of Garlic Oil from *Allium sativum* L. *IOP Conf. Ser. Mater. Sci. Eng.* **2019**, *673*, 012005. [[CrossRef](#)]
54. Cardoso, A.L.; Neves, S.C.G.; da Silva, M.J. Esterification of Oleic Acid for Biodiesel Production Catalyzed by SnCl<sub>2</sub>: A Kinetic Investigation. *Energies* **2008**, *1*, 79–92. [[CrossRef](#)]
55. Da Silva, M.J.; Julio, A.A.; Dos Santos, K.T. Sn(II)-Catalyzed  $\beta$ -Citronellol Esterification: A Brønsted Acid-Free Process for Synthesis of Fragrances at Room Temperature. *Catal. Sci. Technol.* **2015**, *5*, 1261–1266. [[CrossRef](#)]
56. Marso, T.M.M.; Kalpage, C.S.; Udugala-Ganeheneg, M.Y. Metal Modified Graphene Oxide Composite Catalyst for the Production of Biodiesel via Pre-Esterification of *Calophyllum Inophyllum* Oil. *Fuel* **2017**, *199*, 47–64. [[CrossRef](#)]
57. Derringer, G.; Suich, R. Simultaneous Optimization of Several Response Variables. *J. Qual. Technol.* **1980**, *12*, 214–219. [[CrossRef](#)]
58. Park, S.H.; Park, J.O. Simultaneous Optimization of Multiple Responses Using. In *Quality Improvement Through Statistical Methods*; Abraham, B., Ed.; Springer Science: New York, NY, USA, 1998; pp. 299–300.
59. Aziz, N.A.; AS, N.A.; Noraziman, S. Modified Desirability Function For Optimization of Multiple Responses Nasuhar. *J. Math. Comput. Sci.* **2018**, *1*, 39–54.
60. Amdoun, R.; Khelifi, L.; Khelifi-Slaoui, M.; Amroune, S.; Asch, M.; Assaf-ducrocq, C.; Gontier, E. The Desirability Optimization Methodology; a Tool to Predict Two Antagonist Responses in Biotechnological Systems: Case of Biomass Growth and Hyoscyamine Content in Elicited *Datura Stramonium* Hairy Roots. *Iran. J. Biotechnol.* **2018**, *16*, 11–19. [[CrossRef](#)]

**Disclaimer/Publisher’s Note:** The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.

# Conversion of Free Fatty Acid in Calophyllum inophyllum Oil to Fatty Acid Ester as Precursor of Bio-Based Epoxy Plasticizer via SnCl<sub>2</sub>-Catalyzed Esterification

## ORIGINALITY REPORT

13%

SIMILARITY INDEX

7%

INTERNET SOURCES

11%

PUBLICATIONS

3%

STUDENT PAPERS

## PRIMARY SOURCES

- 1 Ke Zhao, Bang Chen, Cong Li, Chao-shuang Xia, Xing-fu Li, Ke-bin Li, Ye-hua Shen. "Optimization of epoxidation of ricinoleic acid methyl ester by hydrogen peroxide and phase-transfer catalyst using response surface methodology", *European Journal of Lipid Science and Technology*, 2017  
Publication 1%
- 2 [bioresourcesbioprocessing.springeropen.com](http://bioresourcesbioprocessing.springeropen.com)  
Internet Source 1%
- 3 C C S Nindya, D R Anggara, Nuryoto, K Teguh. "Esterification glycerol (by product in biodiesel production) with oleic acid using mordenite natural zeolite as catalyst: study of reaction temperature and catalyst loading effect", *IOP Conference Series: Materials Science and Engineering*, 2020  
Publication 1%
- 4 [link.springer.com](http://link.springer.com)  
Internet Source

1 %

5

Ratna Dewi Kusumaningtyas, Muhammad Yasir Adhi Utomo, Pipit Risky Nurjanah, Dwi Widjanarko. "Synthesis of biodiesel from kapok (Ceiba pentandra L.) seed oil through ultrasound-enhanced transesterification reaction", AIP Publishing, 2020

Publication

1 %

6

[repository.uwc.ac.za](https://repository.uwc.ac.za)

Internet Source

1 %

7

[ir.uitm.edu.my](https://ir.uitm.edu.my)

Internet Source

<1 %

8

Submitted to Universiti Malaysia Perlis

Student Paper

<1 %

9

[journal.unnes.ac.id](https://journal.unnes.ac.id)

Internet Source

<1 %

10

[journals-jd.upm.edu.my](https://journals-jd.upm.edu.my)

Internet Source

<1 %

11

[www.rsc.org](https://www.rsc.org)

Internet Source

<1 %

12

[www.nature.com](https://www.nature.com)

Internet Source

<1 %

13

Reza Abbasinejad, Dariusz Kacprzak. "A comprehensive detailed formula for LED

<1 %



degradation and lifetime estimation leading to reduce CO2 emissions", Cleaner Engineering and Technology, 2022

Publication

14

[www.vup.sk](http://www.vup.sk)

Internet Source

<1 %

15

Shuzhen Sun, Liping Zhang, Xin Meng, Zhong Xin. "Kinetic study on lipase catalyzed transesterification of palm oil and dimethyl carbonate for biodiesel production", Journal of Renewable and Sustainable Energy, 2013

Publication

<1 %

16

[umpir.ump.edu.my](http://umpir.ump.edu.my)

Internet Source

<1 %

17

[conference.unsri.ac.id](http://conference.unsri.ac.id)

Internet Source

<1 %

18

"Biorefinery of Oil Producing Plants for Value - Added Products", Wiley, 2022

Publication

<1 %

19

R. Saetang, M. Altamirano, L. B. Romero-Zerón. "Formulation of an Organic Base Catalyst with Animal Shells and Metal Oxide for Biodiesel Production", Energy Sources, Part A: Recovery, Utilization, and Environmental Effects, 2010

Publication

<1 %

20

Z Karami, MJ Zohuriaan-Mehr, K Kabiri, N Ghasemi Rad. "Bio-based thermoset alloys from epoxy acrylate, sesame oil- and castor oil-derived resins: Renewable alternatives to vinyl ester and unsaturated polyester resins", *Polymers from Renewable Resources*, 2019

Publication

&lt;1 %

21

"Biodiesel Technology and Applications", Wiley, 2021

Publication

&lt;1 %

22

Rania F. Khedr. "Radiation-Grafting on Polypropylene Copolymer Membranes for Using in Cadmium Adsorption", *Polymers*, 2023

Publication

&lt;1 %

23

Abdul Qadeer, Kelly L Kirsten, Zeeshan Ajmal, Xia Jiang, Xingru Zhao. "Alternative Plasticizers As Emerging Global Environmental and Health Threat: Another Regrettable Substitution?", *Environmental Science & Technology*, 2022

Publication

&lt;1 %

24

Aijaz Baig, Flora T. T. Ng. " A Single-Step Solid Acid-Catalyzed Process for the Production of Biodiesel from High Free Fatty Acid Feedstocks ", *Energy & Fuels*, 2010

Publication

&lt;1 %

25

Ashish Mohod, Nishant Bhaskar, Vinayak Rajan, Ramansingh Thakur, Manisha Bagal. "Intensified Synthesis of Biodiesel using low-cost feedstock and catalyst via Conventional as well as Ultrasonic Irradiation based approach", South African Journal of Chemical Engineering, 2020

Publication

&lt;1 %

26

Tan, I.A.W.. "Optimization of preparation conditions for activated carbons from coconut husk using response surface methodology", Chemical Engineering Journal, 20080415

Publication

&lt;1 %

27

Submitted to University of Witwatersrand

Student Paper

&lt;1 %

28

Weijie Zhang, Pingping Jiang, Ying Wang, Jian Zhang, Pingbo Zhang. "Manganese(III) Tetrphenylporphyrin Encapsulated by Ion-Modified Hexagonal Mesoporous Silica With Unexpected Enhanced Epoxidation Selectivity", Synthesis and Reactivity in Inorganic, Metal-Organic, and Nano-Metal Chemistry, 2016

Publication

&lt;1 %

29

[article.foodnutritionresearch.com](http://article.foodnutritionresearch.com)

Internet Source

&lt;1 %

30 Adriana Freites Aguilera, Pasi Tolvanen, Shuyana Heredia, Marta González Muñoz et al. "Epoxidation of Fatty Acids and Vegetable Oils Assisted by Microwaves Catalyzed by a Cation Exchange Resin", Industrial & Engineering Chemistry Research, 2018  
Publication

---

31 Jing-Li Zhao, Meiping Zhang, Hong-Li Zhou. "Microwave-Assisted Extraction, Purification, Partial Characterization, and Bioactivity of Polysaccharides from Panax ginseng", Molecules, 2019  
Publication

---

32 R. Naveenkumar, G. Baskar. "Biodiesel production from Calophyllum inophyllum oil using zinc doped calcium oxide (Plaster of Paris) nanocatalyst", Bioresource Technology, 2019  
Publication

---

33 [studentsrepo.um.edu.my](http://studentsrepo.um.edu.my)  
Internet Source

---

34 Submitted to Adtalem Global Education  
Student Paper

---

35 Hameed, B.H.. "Preparation of oil palm empty fruit bunch-based activated carbon for removal of 2,4,6-trichlorophenol: Optimization

using response surface methodology", Journal of Hazardous Materials, 20090530

Publication

36

Mohamad Firdaus Mohamad Yusop, Mohd Azmier Ahmad, Nur Ayshah Rosli, Mohd Edeerozey Abd Manaf. "Adsorption of cationic methylene blue dye using microwave-assisted activated carbon derived from acacia wood: Optimization and batch studies", Arabian Journal of Chemistry, 2021

Publication

<1 %

37

[irjaes.com](http://irjaes.com)

Internet Source

<1 %

38

[pubag.nal.usda.gov](http://pubag.nal.usda.gov)

Internet Source

<1 %

39

[repository.i3l.ac.id](http://repository.i3l.ac.id)

Internet Source

<1 %

40

Abha Sahu, Aniruddha B. Pandit. "Kinetic Study of Homogeneous Catalyzed Esterification of a Series of Aliphatic Acids with Different Alcohols", Industrial & Engineering Chemistry Research, 2019

Publication

<1 %

41

Babadi, Farahnaz Eghbali, Soraya Hosseini, Salman Masoudi Soltani, Mohamed Kheireddine Aroua, Ahmad Shamiri, and Mahtab Samadi. "Sulfonated Beet Pulp as

<1 %



Solid Catalyst in One-Step Esterification of Industrial Palm Fatty Acid Distillate", Journal of the American Oil Chemists Society, 2015.

Publication

---

42

Binta Hadi Jume, Mohammad Ali Gabris, Hamid Rashidi Nodeh, Shahabaldin Rezania, Jinwoo Cho. "Biodiesel production from waste cooking oil using a novel heterogeneous catalyst based on graphene oxide doped metal oxide nanoparticles", Renewable Energy, 2020

Publication

---

<1 %

43

Patrycja Wojciechowska. "Chapter 9 The Effect of Concentration and Type of Plasticizer on the Mechanical Properties of Cellulose Acetate Butyrate Organic-Inorganic Hybrids", IntechOpen, 2012

Publication

---

<1 %

44

Saxon Paiz, José Martim Costa Junior, Péricles Crisiron Pontes, Juliana Damasceno da C. G. de Carvalho et al. "Experimental parametric analysis of biodiesel synthesis in microreactors using waste cooking oil (WCO) in ethylic route", Journal of the Brazilian Society of Mechanical Sciences and Engineering, 2022

Publication

---

<1 %

45 Thirugnanasambandham Karchiyappan, Rekha Pachaiappan. "Protein recovery from sweet potato starch wastewater using modified chitosan", Journal of Applied Water Engineering and Research, 2022  
Publication <1 %

---

46 Varinrumpai Seithtanabutara, Chatuphong Sungnat, Tanakorn Wongwuttanasatian. "Comparison of free fatty acid conversion yields for esterification assisted by single- and dual-frequency sonication", Biomass Conversion and Biorefinery, 2020  
Publication <1 %

---

47 Zarmeena Khan, Fahed Javed, Zufishan Shamair, Ainy Hafeez, Tahir Fazal, Ambreen Aslam, William B. Zimmerman, Fahad Rehman. "Current developments in esterification reaction: A review on process and parameters", Journal of Industrial and Engineering Chemistry, 2021  
Publication <1 %

---

48 [atrium.lib.uoguelph.ca](http://atrium.lib.uoguelph.ca)  
Internet Source <1 %

---

49 [www.jpsr.pharmainfo.in](http://www.jpsr.pharmainfo.in)  
Internet Source <1 %

---

50 [www.jurnal.unsyiah.ac.id](http://www.jurnal.unsyiah.ac.id)  
Internet Source <1 %

---

---

Exclude quotes      On

Exclude matches      < 10 words

Exclude bibliography      On

# Conversion of Free Fatty Acid in Calophyllum inophyllum Oil to Fatty Acid Ester as Precursor of Bio-Based Epoxy Plasticizer via SnCl<sub>2</sub>-Catalyzed Esterification

---

## GRADEMARK REPORT

---

FINAL GRADE

**/0**

GENERAL COMMENTS

**Instructor**

---

PAGE 1

---

PAGE 2

---

PAGE 3

---

PAGE 4

---

PAGE 5

---

PAGE 6

---

PAGE 7

---

PAGE 8

---

PAGE 9

---

PAGE 10

---

PAGE 11

---

PAGE 12

---

PAGE 13

---

PAGE 14

---

PAGE 15

---